

Preparation and Application of KOH Impregnated Sepiolite as a Solid Base Catalyst for Biodiesel Production Using Microwave Irradiation

M. Hamdi Karaoğlu

Muğla Sıtkı Koçman Üniversitesi: Mugla Sıtkı Kocman Universitesi

Vladimir Zholobenko

Keele University

Sema Aslan (✉ sozcan87@gmail.com)

Muğla Sıtkı Koçman Üniversitesi: Mugla Sıtkı Kocman Universitesi <https://orcid.org/0000-0001-9796-7311>

Research

Keywords: Heterogenous catalysis, KOH, sepiolite, rapeseed oil, microwave assisted transesterification, biodiesel production

Posted Date: May 4th, 2021

DOI: <https://doi.org/10.21203/rs.3.rs-392791/v1>

License:   This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Abstract

An active basic solid catalyst for biodiesel production was obtained via KOH impregnation onto sepiolite support followed by high temperature calcination. The transesterification of rapeseed oil over the resulting nanocomposite structure was investigated using a microwave reactor. Morphological and structural characterization of sepiolite and KOH impregnated sepiolite was carried out by Fourier transform infrared spectroscopy, X-ray diffraction, scanning electron microscopy and energy dispersive spectroscopy analysis. Optimization of the operational parameters such as methanol to oil molar ratio, catalyst loading, reaction temperature and reaction time were examined. Reusability of the catalyst and the reactions utilizing waste cooking oil were also studied. Obtained results indicated that the basic heterogenous catalysis diminishes the saponification during the transesterification reaction and that microwave heating was very effective at shortening the biodiesel production time. However, the reusability of the KOH impregnated sepiolite catalysts and their structural stability require further investigation.

1. Introduction

The intension of this article is to explain the benefits of the microwave based transesterification process. The advantages of this system can be listed as rapid heating and cooling, cost saving due to energy and time saving, effective and selective heat control opportunities and short reaction times [1–5].

Transesterification (or alcoholysis), is a chemical reaction between an oil or fat with a suitable alcohol to produce esters and glycerol. This process is composed of three consecutive reversible reactions. At first step triglyceride is converted into diglyceride, then diglyceride is converted into mono glyceride and in the last step monoglyceride is converted to fatty acid alkyl ester and glycerol [6–8].

Homogenous or heterogenous catalysts are utilized in these reaction steps [9]. In a typical homogenous catalyst supported transesterification process, the catalyst is dissolved in the medium completely and there is no phase difference between the catalyst and the reaction mixture. On the other hand, heterogenous catalysis is carried out with a catalyst that form another phase such as solid, immiscible liquid or gaseous in the transesterification medium without passing into the same phase [10, 11]. In this case heterogenous transesterification process is attributed to be a green technology issue due to the recycling facilities of heterogenous catalysts, trace amounts of water production during the process that causes the corrosion in the parts of engine during operation and the easy phase separation of biodiesel and glycerol in the end of the reaction [12, 13]. Besides, in the homogenous catalytic transesterification, required catalyst amount is very much, since the salts are reacting with fatty acids before alcohol they yield very high saponification numbers, in the end low quality of biodiesel and glycerol, long term process and distillation are acquired for the excess reactant removal [14–17].

A large scale of heterogeneous catalysts such as alkali metal oxides and their derivatives [18–22] alkaline earth metal oxides and their derivatives [21, 23–30], transition metal oxides and their derivatives

[31], mixed metal oxides and their derivatives [32], ion exchange resin using [33, 34] or sulphated oxide acidic catalysts [35, 36], carbon based catalysts [37], boron group based catalysts [32, 38], waste material using catalysts [39], enzyme based catalysts [40] are in the ascendant in laboratory scale biodiesel production. In a KOH or KOH-bentonite [41] mixture using transesterification study the author claimed that the obtained fatty acid methyl ester (FAME) content, which defines the quality of the biodiesel, increased with the increasing amounts of bentonite proportions [42]. Since the bentonite bears some active groups (such as SiO_2 Al_2O_3 Fe_2O_3 CaO MgO K_2O Na_2O), it chokes the water production and can trigger the presence of catalytically active methoxides during the methanolysis process by shifting the reaction direction in hydroxide/methoxide equilibrium (Eq. (1)) towards the formation of the methoxide, leading to increased amounts of FAME.



Sepiolite is also a good candidate for this purpose by possessing very much similar active catalytic groups such as SiO_2 , MgO or Al_2O_3 and must be used in the same manner with bentonite. Menor et al. reported that MgO presence dominates the basic structure of the bentonite and glycerol production is improved by the combination with Ni impregnation onto this support [43]. We have also enhanced the basic capability of sep. with KOH addition into this unique structure. Additionally, there are several catalytic studies on sepiolite such as CaO loaded sepiolite used as CO_2 sorbent [44], acid-activated sepiolite using glycerol production study [45] or another report claimed that using the sepiolite as additive into the slurries during catalyst preparation revealed with positive results because of enhancing adherence [46].

However, there is not any study about KOH impregnated sepiolite based heterogenous catalysis based on direct biodiesel production with the combination of microwave assistance. There are several methods for the biodiesel production but the crucial point is the choice of the best system avoid to time, energy, yield and quality wasting processes. It is reported that microwave assisted system using production times are lowered up to 6 folds compared to the traditional heating processes [47]. Here we also obtained satisfactory results after 20 min. operation times compared to the previously used 3h. heating process. On the other hand, as we take a deep look into kinetics of this catalyst it can be said that according to the transesterification reaction (Eq. 2) the limiting step is methoxide formation step. In this step the excess amount of methanol addition into the medium doesn't effect at all the order of the reaction. So the calculations can be carried out according to 1st order reaction equation. After the optimization studies reusability and waste rapeseed oil transesterification performances of the present system was tried. This study can be evaluated as a demo of the improvable performance of the presented system, the results can be improved by the incubation of final biodiesel-glycerol mixture for phase separation.

2. Experimental

2.1. Chemical Reagents and Equipments

Magnesium sulfate (99.00 % pure), n-hexane (99.00 % pure), methanol (99.80 % pure), and potassium hydroxide (99.00 % pure) were purchased from Merck Co. Sepiolite was supplied from Sigma-Aldrich, edible rapeseed oil was bought from a local market. FTIR spectra were collected using a Thermo iS10 spectrometer, XRD patterns which were recorded on a Bruker D8 Advance diffractometer TM3000 (Hitachi) scanning electron microscopy (SEM) with energy dispersive X-ray analysis (EDX, Bruker) was utilised to obtain the elemental composition of the sepiolites, biodiesel reaction studies were performed in a Biotage microwave system (Biotage Initiator+).

2.2. Catalyst Preparation and characterization

The first step of the KOH impregnated sepiolite catalyst synthesis is the choice of the KOH/sepiolite ratio. It was defined as 1:4, then the aqueous solution of KOH salt was added into sepiolite containing three-necked flask. Modification of the catalyst was performed with wet impregnation method in which, aqueous solution of potassium hydroxide salt applied onto the sepiolite support. A round bottom three-necked flask (500 mL) was utilized in the synthesis of the catalyst. The flask was donated with a reflux condenser to keep the solvent inside, a thermometer to measure the temperature during the reaction and a mechanical stirrer to mix the suspension with a magnetic bar. The impregnation of sepiolite with KOH was achieved under continuous stirring for 24 h at a temperature of 60°C. After the impregnation process, obtained catalyst was centrifuged, filtrated and calcined at 400°C for 5 h. Then, these samples were cooled to room temperature in adessicator and stored at dark medium when not in use [48].

2.3. Transesterification reaction and analysis methods of biodiesel

Transesterification is the key step of the whole biodiesel production process. Especially, if the methoxy formation step does not processed well, FAME yield of the produced biodiesel will be lower than it is expected. In the microwave assisted method, methanol, canola oil and a defined amount (optimal amount) of the catalyst were added into the flask and transferred into the reactor. The mixture was stirred continuously and irradiated at defined (optimal) temperature during the optimum time. Then the resulting biodiesel and glycerol containing mixture was cooled down to the room temperature. Subsequently, it was centrifuged for 15 min at 5000 rpm. The supernatant solution, mainly biodiesel containing part of the sample was separated and washed. In order to remove the remaining humidity in the biodiesel, a spatula of magnesium sulphate anhydrous salt was added into the vessel and centrifuged again. Finally, the sample was analyzed by GC-MS to define the total FAME ingredient and concentration [49].

3. Results And Discussion

3.1. Structural characterizations of the catalyst

The FT-IR spectra is a conventional method to enlighten the bond formation of the catalysts. Supplementary Fig. 1 shows the FTIR spectra of raw sepiolite and KOH/sep. It is clear to indicate that the OH bending peak of the external surface (3558.59 cm^{-1}) (Supplementary Fig. 1a) belongs to raw

sepiolite was suppressed after the modification (Supplementary Fig. 1b). The peak at the 1659.22 cm^{-1} was shifted to the 1648.57 cm^{-1} corresponding the change of the OH vibrations in the sepiolite structure. Also the 1209.98 cm^{-1} peak was diminished due to this recombination of the zeolitic OH group. Finally, the peak shifts in the finger print area (687.65 and 969.72 cm^{-1}) were attributed to the metallic load onto the sepiolite structure and resulted as change in the Si-O-Si plane vibrations [50, 51].

Raw and modified sepiolites, discussed above were morphologically studied using SEM-EDX (Fig. 1). When SEM images belonging to KOH/sep material are analyzed, it is seen that clear colour removal has occurred and surface pores were doped when compared to raw sepiolite. This colour changes leads us to think that K_2O is considerably adsorbed in sepiolite surface and pores (Fig. 1a SEM image of the raw sepiolite, b) SEM image of the KOH/sep.). Additionally, the elemental EDX peak of the K in the KOH/sep. structure showed increment after the modification (Fig. 1c: raw sepiolite, Fig. 1d: KOH/sep.). The impregnation of sepiolite with KOH is evaluated to be successful after these morphological measurement results. Atomic weight percentages of EDX measurements are also given in the Table 1.

Table 1
Atomic weight percentages of EDX measurements

Type of element	Natural sepiolite (wt %)	KOH impregnated sepiolite (wt %)
Si	23.32	21.70
Mg	13.78	11.69
K	3.12	1.14
Al	1.54	0.38

XRD curves of raw sepiolite and KOH/sep. are illustrated in Fig. 2. As Fig. 2b indicates, the treatment of sepiolite with KOH altered their crystalline structure, since the original crystalline peaks diminished significantly in intensity. XRD pattern of natural sepiolite (Fig. 2a) shows the typical diffraction peaks at $2\theta = 7.0^\circ, 19.55^\circ, 20.40^\circ, 23.55^\circ, 26.55^\circ, 27.95^\circ, 34.80^\circ, 36.40^\circ, 40.0^\circ$ and 48.20° . The presence of K_2O after the modification (Fig. 2b) was indicated by the intensity peaks at 2θ at $6.85^\circ, 26.30^\circ, 27.50^\circ, 34.40^\circ, 36.40^\circ, 39.45^\circ, 41.25^\circ, 42.65^\circ, 45.90^\circ$ and 48.30° .

3.2. Evaluation of the Catalytic Performance of KOH/sep. modified catalyst using microwave irradiation

According to the interaction of dielectric nature of the materials with microwaves leads to electronic, ionic, dipole or interfacial polarization of the substance. This type of heating mechanism leads to dielectric heating of the substance at each polarization station not likely conventional heating systems (Scheme 1). The usage of microwave irradiation enhances the reaction stations of the triglycerides.

Methanol is mostly used as solvent in transesterification reactions, known to have high microwave absorption capacity. Since its high polarity feature it can be concluded that oil-methanol-catalyst involved reaction can be effected by microwaves by dipolar polarization and ionic conduction. Ionic or dipole

rotations of the molecules ease the collisions between methanol and oil so this interaction results in superheating of the reaction stations of the triglycerides (Scheme 1) [2, 8].

The effect of catalyst loading on the biodiesel yield was studied with the different weight percentages of the catalyst (Fig. 3a). Here the weights of KOH/sep. were chosen from 3–9% whereas other conditions were maintained as MeOH/oil molar ratio of 1/6, reaction time 20 min. and temperature 80 °C. The biodiesel yields were clearly increased from 0.32 to 57.14 % according to the amount of catalyst increased from 3 to 9 wt%. This increment shows that the collisions between catalyst surface and the triglyceride at 9%, are definitely much more than that of 3% [52].

The temperature is an important parameter in catalytic studies and its effect should be investigated for transesterification reaction that is catalysed by a solid catalyst [53]. The effect of temperature on the esterification using the microwave approach has been investigated by changing the temperature of reaction at different values as 60, 80 and 100 °C (Fig. 3b). The MeOH/oil molar ratio of 1/6 and catalyst concentration of 3% (w/w) was kept constant for all the experimental runs related to the effect of temperature. Figure 3 shows the conversion rate of biodiesel increased when the reaction temperature increased from 333 to 393 K.

Biodiesel production from transesterification is a reversible reaction. The biodiesel yield could be improved by introducing excess amounts of methanol to force the reaction towards the formation of biodiesel [53]. The methanol/oil molar ratio ranged from 3:1 to 9:1 were used for biodiesel production at given conditions (Fig. 3c) (catalyst amount 3 wt.%, reaction time 20 min and temperature 80 °C). The yield increased from 7.42–21.20% with the increase in molar ratio from 3:1 to 9:1.

Effect of reaction time was studied by varying time intervals (Fig. 3c). Studies were carried out at different irradiation times, e.g. 5, 10, 20 and 30 minute with 3.0% catalyst and methanol/oil molar ratio: 6/1. The effect of reaction time on the transesterification reaction is presented in Fig. 3. The conversion rate of biodiesel increased from 10.53–57.21% when the reaction time increased from 5 min. to 30 min..

4. Conclusion

In this study, biodiesel is produced from canola oil using microwave assisted transesterification process. It is very important to reach effective transesterification yields in a short reaction time. Among the methods developed until today this is an intermediate study that indicates the effectiveness of microwave assistance in the biodiesel production. The optimal reaction levels were defined as a methanol/oil molar ratio of 9:1, amount of catalyst of 9.0 wt.% and reaction temperature at 353 K for a 20 min transesterification reaction. In the end 57.14 % biodiesel yield was achieved. The use of microwave irradiation always shortened the reaction time and was provided higher FAME yields. However, the reusability of the KOH impregnated sepiolite catalysts and their structural stability requires further investigation.

Declarations

The authors declare that there are no competing interests.

Availability of data and materials

The data used to support the findings of this study are available from the corresponding author upon request.

Acknowledgements

Tubitak is gratefully acknowledged by the authors.

Funding

The presented study was financially supported by the Tubitak 2219 International Post Doctoral Research Fellowship Programme.

Contributions

MHK and VZ contributed in the project administration and formal analysis, SA contributed in the writing - original draft.

References

1. Hong IK, Jeon H, Kim H, Lee SB. Preparation of waste cooking oil based biodiesel using microwave irradiation energy. *Journal of Industrial and Engineering Chemistry* 2016; 42:107–112.
2. Fatimah I, Rubiyanto D, Nugrah J. Preparation, characterization, and modelling activity of potassium fluoride modified hydrotalcite for microwave assisted biodiesel conversion. *Sustainable Chemistry and Pharmacy* 2018; 8:63–70.
3. Hoang AT, Tabatabaei M, Aghbashlo M. A review of the effect of biodiesel on the corrosion behavior of metals/alloys in diesel engines. *Energy Sources, Part A: Recovery, Utilization, and Environmental Effects* 2019; 42: 2923–2943 DOI: 10.1080/15567036.2019.1623346
4. Pasupathy RS, Mohanraj T. A novel approach to utilize esterified rice bran oil as an additive with gasoline and ethanol blends in MPFI SI engine. *Energy Sources, Part A: Recovery, Utilization, and Environmental Effects* 2019; DOI: 10.1080/15567036.2019.1623952
5. Tomar M, Kumar N. Influence of nanoadditives on the performance and emission characteristics of a CI engine fuelled with diesel, biodiesel, and blends – a review. *Energy Sources, Part A: Recovery, Utilization, and Environmental Effects* 2019; 42: 2944–2961. DOI: 10.1080/15567036.2019.1623347
6. Ma F, Hanna MA. Biodiesel production: a review. *Bioresource Technology* 1999 70:1–15.
7. Al-Ani A, Gertisser R, Zholobenko V. Structural features and stability of Spanish sepiolite as a potential catalyst. *Applied Clay Science* 2018a; 162: 297–304.

8. Al-Ani A, Darton RJ, Sneddon S, Zholobenko V. Nanostructured Zeolites: The Introduction of Intracrystalline Mesoporosity in Basic Faujasite-type Catalysts. *ACS Applied Nano Materials* 2018b; 1: 310–318.
9. Wang Y, Wang X, Liu Y, Ou S, Tan Y et al. Refining of biodiesel by ceramic membrane separation. *Fuel Processing Technology* 2009; 90: 422–7.
10. Helwani Z, Othman MR, Aziz N, Kim J, Fernando WJN. Solid heterogeneous catalysts for transesterification of triglycerides with methanol: a review. *Applied Catalysis A: General* 2009; 363: 1–10.
11. Zabeti M, Wan M, Wan D. Activity of solid catalysts for biodiesel production: a review. *Fuel Processing Technology* 2009; 90: 770–7.
12. Sarma AK, Sarmah JK, Barbora L, Kalita P, Chatterjee S et al. Recent inventions in biodiesel production and processing: a review. *Recent Patents on Engineering* 2008; 2: 47–58.
13. Lee JS, Saka S. Biodiesel production by heterogeneous catalysts and supercritical technologies: review. *Bioresource Technology* 2010; 101:7191–200.
14. Canakci M, Van Gerpan J. Biodiesel production from oils and fats with high free fatty acids. *Transactions-American Society of Agricultural Engineers* 2001; 44: 1429–36.
15. Grandos ML, Poves MD, Alonso D, Mariscal R, Galisteo FC et al. Biodiesel from sunflower oil by using activated calcium oxide. *Applied Catalysis B: Environmental* 2007; 73: 317–26.
16. Ji J, Wang J, Li Y, Yu Y, Xu Z. Preparation of biodiesel with the help of ultrasonic and hydrodynamic cavitation. *Ultrasonics* 2006; 44: 411–4.
17. Kumar KS, Anju C. Preparation of biodiesel from crude oil of *Pongamia pinnata*. *Bioresource Technology* 2005; 96: 1425–9.
18. Ebiura T, Echizen T, Ishikawa A, Kazuhito M, Baba T. Selective transesterification of triolein with methanol to methyl oleate and glycerol using alumina loaded with alkali metal salt as a solid-base catalyst. *Applied Catalysis A: General* 2005; 283: 111–6.
19. Xie W, Hong P, Ligong C. Calcined Mg–Al hydrotalcites as solid base catalysts for methanolysis of soybean oil. *Journal of Molecular Catalysis A: Chemical* 2006; 246: 24–32.
20. Fabbri D, Bevoni V, Notari M, Rivetti F. Properties of a potential biofuel obtained from soybean oil by transmethylation with dimethyl carbonate. *Fuel* 2007; 86: 690–7.
21. Wang L, Yang J. Transesterification of soybean oil with nano-MgO or not in supercritical and subcritical methanol. *Fuel* 2007; 86: 328–33.
22. Arzamendi G, Campoa I, Arguinarena E, Sanchez M, Montes M et al. Synthesis of biodiesel with heterogeneous NaOH/alumina catalysts: comparison with homogeneous NaOH. *Chemical Engineering Journal* 2007; 134: 123–30.
23. Lopez DE, Bruce Jr DA, Lotero JGE. Transesterification of triacetin with methanol on solid acid and base catalysts. *Applied Catalysis A: General* 2005; 295: 97–105.

24. Tateno T, Sasaki T. Process for producing fatty acid fuels comprising fatty acids esters. Uni. State Patent 6818026, November 16, 2004.
25. Di Serio M, Tesser R, Dimiccoli M, Cammarota F, Nasatani M et al. Synthesis of biodiesel via homogeneous Lewis acid catalysts. *Journal of Molecular Catalysis* 2005; 239: 111–5.
26. Mootabadi H, Salamatinia B, Bhatia S, Abdullah AZ. Ultrasonic-assisted biodiesel production process from palm oil using alkaline earth metal oxides as the heterogeneous catalysts. *Fuel* 2010; 89: 1818–25.
27. Salamatinia B, Mootabadi H, Bhatia S, Abdullah AZ. Optimization of ultrasonic-assisted heterogeneous biodiesel production from palm oil: a response surface methodology approach. *Fuel Processing Technology* 2010; 91: 441–8.
28. Vujicic DJ, Comic D, Zarubica A, Micic R, Boskovic G. Kinetics of biodiesel synthesis from sunflower oil over CaO heterogeneous catalyst. *Fuel* 2010; 89: 2054–61.
29. Yoosuk B, Udomsap P, Buppa P, Pawnprapa K. Modification of calcite by hydration–dehydration method for heterogeneous biodiesel production process: the effects of water on properties and activity. *Chemical Engineering Journal* 2010; 162: 135–41.
30. Yoo SJ, Lee HS, Bambang V, Kim J, Kim JD et al. Synthesis of biodiesel from rapeseed oil using supercritical methanol with metal oxide catalysts. *Bioresource Technology* 2010; 101: 8686–9.
31. Antunes WM, Veloso CO, Henriques CA. Transesterification of soybean oil with methanol catalyzed by basic solids. *Catalysis Today* 2008; 133–135: 548–54.
32. Ilgen O. Dolomite as a heterogeneous catalyst for transesterification of canola oil. *Fuel Processing Technology* 2011; 92: 452–5.
33. Alsalmeh A, Kozhevnikova EF, Kozhevnikov IV. Heteropoly acids as catalysts for liquid-phase esterification and transesterification. *Applied Catalysis A: General* 2008; 349: 170–6.
34. Park YM, Lee D, Kim DK, Lee J, Lee KY. The heterogeneous catalyst system for the continuous conversion of free fatty acids in used vegetable oils for the production of biodiesel. *Catalysis Today* 2008; 131: 238–43.
35. Park YM, Chung S, Eom HJ, Lee J, Lee K. Tungsten oxide zirconia as solid superacid catalyst for esterification of waste acid oil (dark oil). *Bioresource Technology* 2010; 101: 6589–93.
36. Alba-Rubio AC, Vila F, Alonso DM, Ojeda M, Mariscal R et al. Deactivation of organosulfonic acid functionalized silica catalysts during biodiesel synthesis. *Applied Catalysis B: Environmental* 2010; 95: 279–87.
37. Dehkhoda AM, West AH, Ellis N. Biochar based solid acid catalyst for biodiesel production. *Applied Catalysis A: General* 2010; 382: 197–204.
38. Guo C, Baishan F. Preparation of solid acid catalyst from glucose – starch mixture for biodiesel production. *Bioresource Technology* 2011; 102: 2635–40.
39. Deka DC, Basumatary S, Lee JS. High quality biodiesel from yellow oleander (*Thevetia peruviana*) seed oil. *Biomass and Bioenergy* 2011; 305: 1797–803.

40. Chakraborty R, Bepari S, Banerjee A. Application of calcined waste fish (*Labeo rohita*) scale as low-cost heterogeneous catalyst for biodiesel synthesis. *Bioresource Technology* 2011; 102:3610–8.
41. Agarwal M, Chauhan G, Chaurasia SP, Singh K. Study of catalytic behavior of KOH as homogeneous and heterogeneous catalyst for biodiesel production. *Journal of the Taiwan Institute of Chemical Engineers* 2012; 43:89–94.
42. Wu L, Wei TY, Tong ZF, Zou Y, Lin ZJ et al. Bentonite-enhanced biodiesel production by NaOH-catalyzed transesterification of soybean oil with methanol. *Fuel Processing Technology* 2016; 144: 334–340.
43. Menor M, Sayas S, Chica A. Natural sepiolite promoted with Ni as new and efficient catalyst for the sustainable production of hydrogen by steam reforming of the biodiesel by-products glycerol. *Fuel* 2017; 193: 351–358.
44. Shi J, Li Y, Zhang Q, Ma X, Duan L et al. CO₂ capture performance of a novel synthetic CaO/sepiolite sorbent at calcium looping conditions. *Applied Energy* 2017; 203: 412–421.
45. Zhou CH, Li GL, Zhuang XY, Wang PP, Tong DS et al. Roles of texture and acidity of acid-activated sepiolite catalysts in gas-phase catalytic dehydration of glycerol to acrolein. *Molecular Catalysis* 2017; 434: 219–231
46. Reyero I, Moral A, Bimbela F, Radosevic J, Sanz O et al. Metallic monolithic catalysts based on calcium and cerium for the production of biodiesel. *Fuel* 2016; 182: 668–676.
47. Aslan S, Aka N, Karaoğlu MH. NaOH impregnated sepiolite based heterogeneous catalyst and its utilization for the production of biodiesel from canola oil. *Energy Sources, Part A: Recovery, Utilization, And Environmental Effects* 2019; 41:290–297.
48. Omar WNNW, Amin NAS. Biodiesel production from waste cooking oil over alkaline modified zirconia catalyst. *Fuel Processing Technology* 2011; 92: 2397–2405.
49. Cobas M, Ferreira L, Sanroman MA, Pazos M. Assessment of sepiolite as a low-cost adsorbent for phenanthrene and pyrene removal: Kinetic and equilibrium studies. *Ecological Engineering* 2014; 40: 287–294.
50. Eren E, Cubuk O, Ciftci H, Eren B, Caglar B. Adsorption of basic dye from aqueous solutions by modified sepiolite: Equilibrium, kinetics and thermodynamics study. *Desalin* 2010; 252: 88–96.
51. Shahraki H, Entezari MH, Goharshadi EK. Sono-synthesis of biodiesel from soybean oil by KF/c-Al₂O₃ as a nano-solid-base catalyst. *Ultrasonics Sonochemistry* 2015; 23: 266–274.
52. Takase M, Chen Y, Liu H, Zhao T, Yang L et al. Biodiesel production from non-edible *Silybum marianum* oil using heterogeneous solid base catalyst under ultrasonication. *Ultrasonics Sonochemistry* 2014; 21: 1752–1762.
53. Wu H, Zhang J, Wei Q, Zheng J, Zhang J. Transesterification of soybean oil to biodiesel using zeolite supported CaO as strong base catalysts. *Fuel Processing Technology* 2013; 109:13–18.

Supplemental Information

Figures

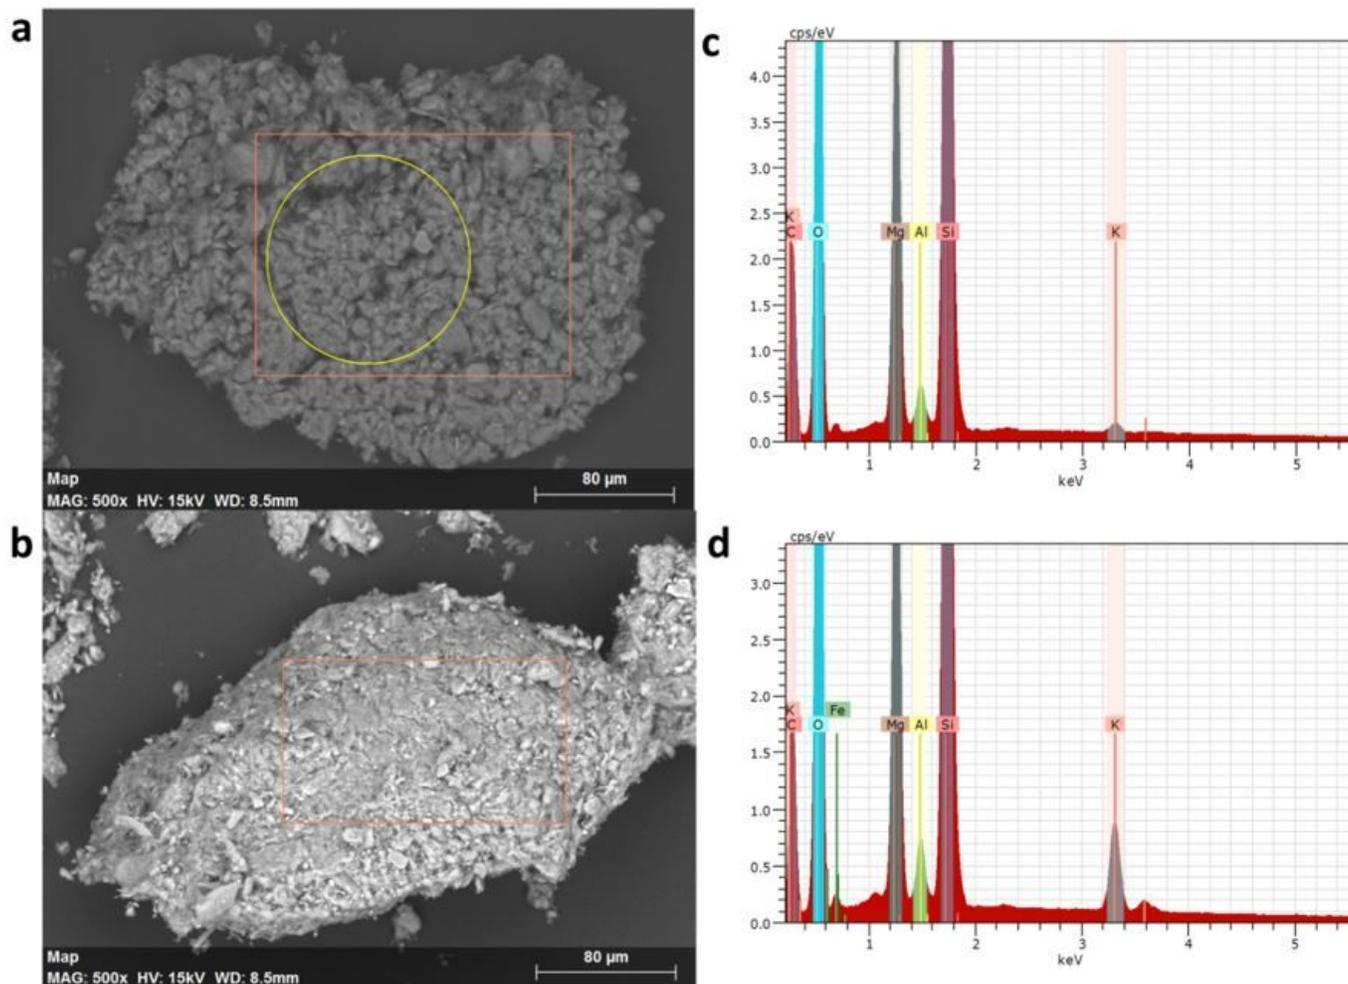


Figure 1

a) SEM image of raw sepiolite, b) SEM image of KOH/sep. c) EDX image of raw sepiolite, d) EDX image of KOH/sep.

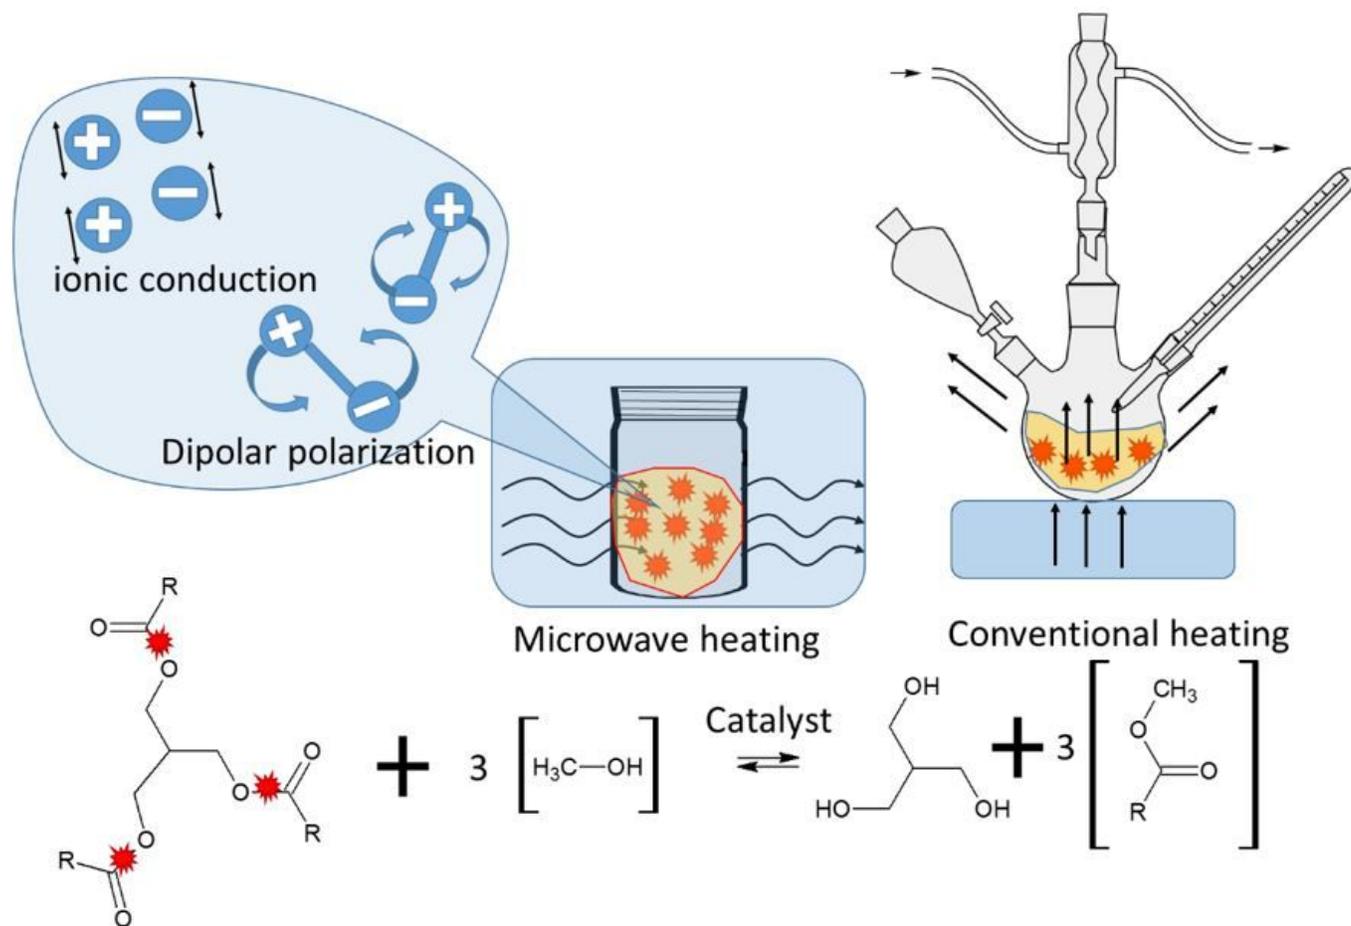


Figure 2

Conventional and microwave heating mechanisms, molecular polarizations of triglycerides under microwave conditions and transesterification reaction scheme.

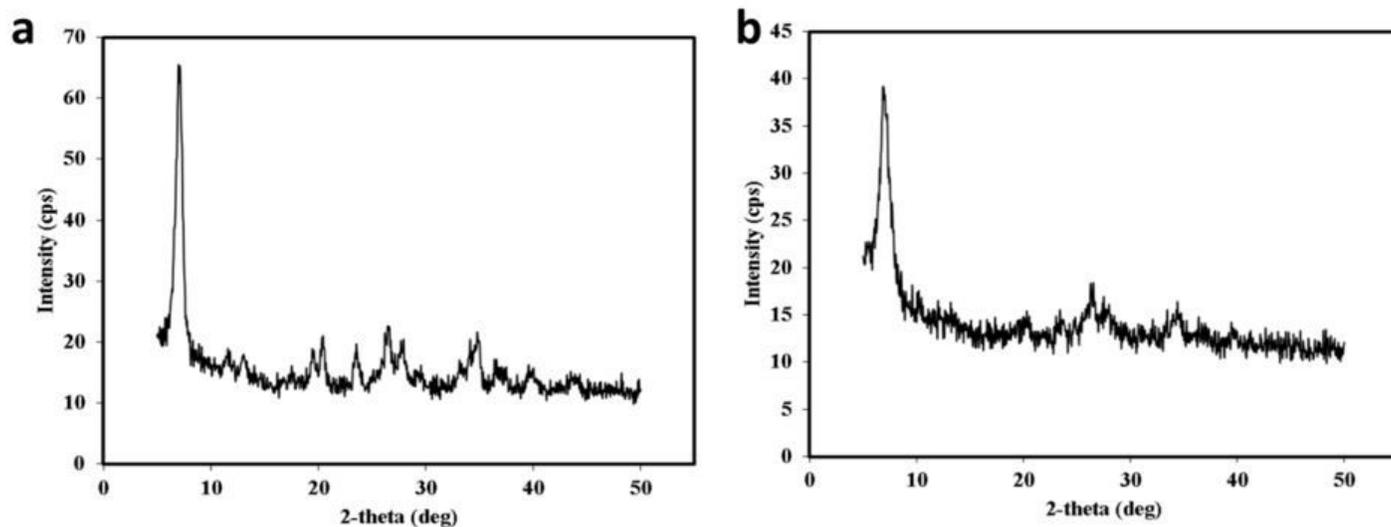


Figure 3

XRD patterns of a) raw sepiolite and b) KOH/sep.

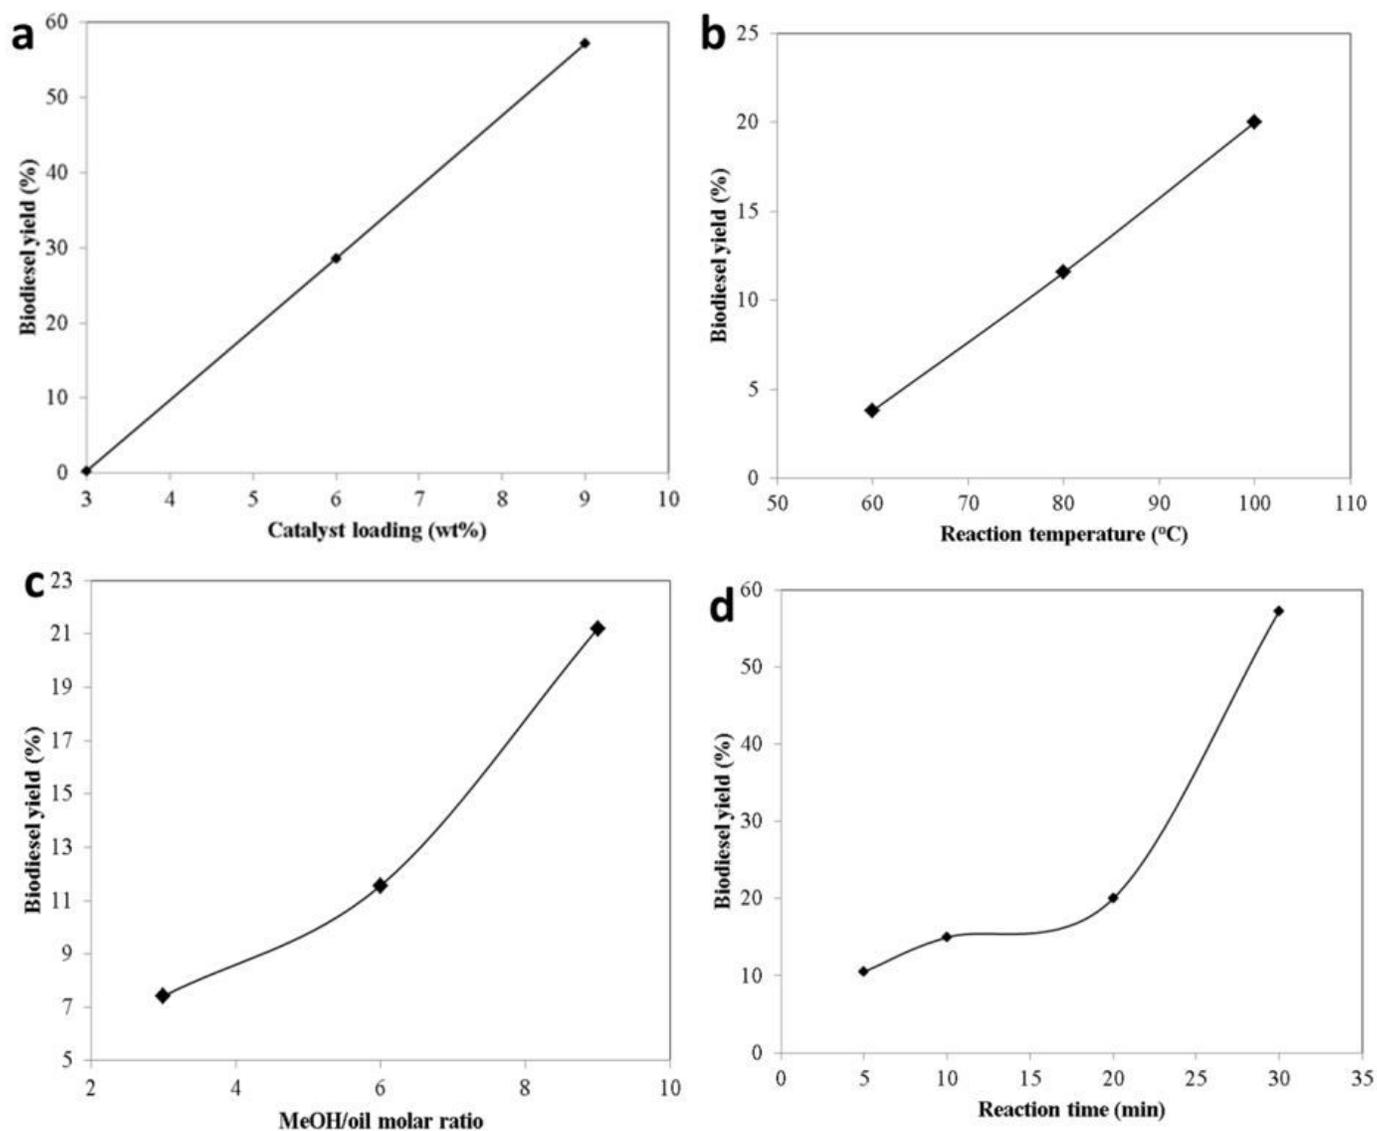


Figure 4

The effects of a) amount of catalyst, b) temperature of the reaction, c) Methanol to oil ratio, d) reaction time on the catalytic performance of KOH/sep. catalyst.