

Development of Shoe Insert for Diabetic Foot Ulcer Patients in Case of Ethiopia.

Awoke fenta Wodag (✉ awokef2005@gmail.com)

Bahir Dar University Institute of Technology for Textile Garment and Fashion Design

Adane Adugna Ayalew

Bahir Dar University

Research

Keywords: Shoe insert, Memory foam, Foot ulcer, Diabetic, Polyurethane, Castor oil

Posted Date: August 12th, 2020

DOI: <https://doi.org/10.21203/rs.3.rs-54003/v1>

License:   This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Abstract

Foot ulcer is mainly developing due to diabetic disease. It is an open sore on the foot. The aim of this research is to develop polyurethane memory foam in sock/shoe insert in Ethiopia by replacing costly material silicon surfactant and distilled water by locally available and affordable input materials castor oil as surfactant and tap water instead of distilled water for the diabetic foot ulcer patients. Under this research, it was able to prove the severity of foot ulcer in Ethiopia and enhance the high demand of orthotic appliance. Three memory foams in sock with different surfactant ratios were manufactured at AMAGA P.L.C foam factory, Bahir Dar Ethiopia using standard Polyols and diisocyanates. The shoe insert /in sock was prepared by using materials used in the factory to prepare PU memory foam mattress with 5g, 9.5 g and 10.36g of castor oil surfactant amount as a new replaced material instead of costly silicon surfactant from the three the first (castor oil 5g is not form a foam and hence no further investigation is conducted on it). Physical properties such as thickness, density, Hardness, Compression set, water absorption and abrasion resistance of developed in sock were tested. Further the new developed in sock was compared with that of existed commercial polyurethane in sock and the SATRA standards. The new developed in sock has showed an equivalent mechanical property with the standard.

Introduction

Foot ulcer is a term that references an open sore that forms on or near one or both of our feet. It may form on the bottom of the foot, the toes, and the top of the foot or even the lower region of the leg mainly caused by diabetic disease [Gebre 2013].According to research result shows about 15% of diabetic patients develop foot ulcers in their lifetime enhancement [Jeon et al.,2010]. Diabetic foot ulcer is becoming major concern of diabetic patients. People with a diabetic foot ulcer (DFU) have a 40% greater 10-year death rate than people with diabetes alone. Foot ulcer problems with diabetic patients account for up to 15% of healthcare resources in developed countries and 40% in developing countries and one in every six people with diabetes will develop ulcer [Tsfatsion et al., 2013].

Poverty and unhygienic conditions associated with foot ulceration are major factors contributing to development of the diabetic foot in developing countries [Deribe. et al. 2013] like Ethiopia. For diabetic patients living at or below poverty line, the purchase of appropriate footwear (orthopedic footwear) might not be affordable, feasible or of high priority [Woldemichael, 2010]. For diabetic foot ulcer patients and people who are overweight, extra pressure may be the cause of ongoing foot pain/ulcer but by using /wearing orthopedic footwear appliance can be redistribute evenly and the development of ongoing foot pain/ ulceration development retards [Zhang.,et al 2017].

The, knees, and back are just some of the body parts that can be adversely affected by improper posture or gait. Orthotics can amend this by spreading the load uniformly around the feet, and then assure that they hit the ground perpendicularly, that why it is so important that cushion memory foam shoe insert is a

need in redistributes our pressure by absorbing shock. Inappropriate footwear and inappropriate insert can have a large share in contributing factor to the development of foot ulceration [Khan, 011]. In the research of diabetic patient's foot ulcer diagnosis, footwear with cushion shoe insert has been implemented to reduce pressure on the foot of diabetic patients, and then its pain status and its result showed very good progress of pain reduction [Armstrong and Lavery, 2005]

Today Memory foam shoe inserts is available commercially at high cost and its source for foot ulcer purpose is imported from developed Countries at high cost. This leads low access, and unable to be used by the low-income patients due to higher cost and consumption of expensive raw materials for production of PU shoe insert /in sock. Hence replacement of castor oil surfactant and tap water in the place of silicon surfactant and distilled water respectively is an optional cost effective way of (PU) Memory in sock production.

Polymer elastomers and foams are mostly used to fit the material properties of shoe appliances, like insole and in sock. Mainly ethylene vinyl acetate (EVA), polyurethane (PU) and rubber based materials are mostly used in footwear [Gebrekidan and Gezahagn, 2016]. PU foams and elastomers are demonstrated as the best effective materials for shock absorption in footwear [Saraswathy, 209] while most are effective when new the softer foam materials have a habit of to deteriorate rapidly with use. Different types of foam are available commercially at high cost. But the available materials are not scientifically characterized and optimized for application as in sock for foot ulcer patients treatment. PU viscoelastic cushion in sock will reduce the foot plantar pressure and give additional cushion support to the foot arches.

Therefore, new Polyurethane (PU) memory foams were developed for application as shoe insert in therapeutic footwear for patients with diabetes. The developed materials were characterized for physical and mechanical properties and PU foam composition was also optimized for application as cushion in sock. The purpose of this study was Developing Polyurethane (PU) Memory Foam In sock and the developed materials were characterized for physical and mechanical property and PU foam composition was also optimized for application as cushion in sock

Materials And Methods

In this study the Polyurethane (PU) Memory Foam In sock was prepared by using standard Polyols, HT, and Isocyanates-toluene di isocyanate (TDI) castor oil, methyl chloride was obtained from research grad textile and leather laboratory. Other additive and auxiliary such as Tin, Thertialy, cross linker; Catalyst, Inorganic filler and cell opener which are physicochemical and environmentally safe were used. The following chemicals specification present in Table1 were derived from AMAGA, P.L.C. Bahir Dar bed foam manufacturing used for Polyurethane (PU) Memory Foam formation at different concentration of castor oil.

Table 1
Bill of raw materials for three pair of in sock / shoe insert sample production

Component		Sample -1	Sample-2	Sample -3
No.	ingredients used	Weight added in (g)	Weight added in (g)	Weight (g)
1	Polyols HT,762	93.3	93.3	93.3
2	Tap water	2*2.6	2*2.6	2*2.6
3	Castor oil surfactant	5	9.5	10.36
4	Tertiary Amine Catalyst	1.7	1.7	1.7
5	Tin Catalyst	1.37	1.37	1.37
6	Cross linkers	8.4	8.4	8.4
7	Isocyanates, TDI	75.5	75.5	75.5
8	Auxiliary blowing agents	4.7	4.7	4.7
Total consumption		199.67g	199.67g	200.5g

Experimental procedure for foam manufacturing

Polyols, reacting agents and tap water were mixed, and stirrer at 30°C temperature for 14 seconds. Isocyanates-toluene Di Isocyanate (TDI) was added and again stirrer for 15 seconds to make sure the reactant was well reacted to their perspective bond. After all, the product was whipped into froth and poured into a mold (test box). An exothermic reaction was resulted which caused the mixture to bubble up and produce foam. The final product foam was cured and takes to store for 8 hours. After curing, memory foam was inert (no longer reactive) and for in sock application, the foam was cut by die for next application.

Physiochemical Characterization

Type of foams with varying density and cushion ability were developed by varying the concentration of surfactant (castor oil). The developed foams were characterized for thickness (mm), density (g/cc) Hardness (mg/L), water absorption (%) Compression set (%) abrasion resistance and pressure redistributing properties of the in sock were required by the material for application as cushion in sock in therapeutic footwear for patients with diabetics.

Plantar pressure distribution test

The plantar pressure reduction and distribution properties of the developed insert/in sock, foam was measured using carbon copy pressure measurement system, and then related with that of ethyl vinyl acetate (EVA) in sock/ shoe insert which was conducted at Leather Industry development institute (LIDI) and Ethiopian institute of textile and Fashion Technology (EiTEX) research laboratory with ELETTRONIC A.B.C machine at 7 bar pressure and analyzed the effect due to the material changes.

Results And Discussion

The physio mechanical properties of PU memory foam are presented in Table 1. It has shown that the initial formulation of PU memory foam in (sample 1) is not foam but as a thick liquid this is due to very low amount (5g) of castor oil as a surfactant is used due to this no further study is done on it and (sample 2) is not suitable for application as cushion in sock / shoe insert for Diabetic foot ulcer due to low hardness, density and low compression but sample three shows a very good properties.

Density:

During measuring density, by taking similar thickness of PU memory foam in sock and size. The density test resulted of samples are presented in Table 1. The test result value for sample 2 was 0.194 g/cm^3 and 0.22 g/cm^3 for sample 3. Hence, sample 3 found between $0.2-0.3 \text{ g/cm}^3$ which is in between SATRA density standards requirements as results show density of PU memory foam in sock which is the newly developed sample 2 is slightly lower than that of existed in sock but approximately confirms the standard, in case of Sample 3 it is much harder than that of sample one but it is still within the range of standard. If the density is below standard requirements the shoe insert will compressed and sticky during use and if it is too high, it consume more material and become costly and less comfort. Material with higher density the higher the load bearing capacity, this implies that the sample 3 has remarkable load bearing capacity and support. Therefore, the replacement of materials silicon surfactant by castor oil surfactant and distilled water by tap water shows a positive effect in this particular property

Table 2
Physical test results of PU memory foams

No.	Properties	Obtained value			
		Sample 2	Sample 3	Commercial insole	SATRA sandaled
1	Density (g/cc)	0.194	0.22	0.253	0.2-0.3
2	Hardness (mg/L)	19.25	21.09	5-7	17-22
3	Thickness (mm)	11	11.5	8	13-14
4	Abrasion resistance (%)	2.98	2.62	6.9	-
5	Compression (%)	3.82	4.2	6.1	5
6	Water absorption (%)	63	52.5	39	30

Hardness:

The mean value of hardness was shown is 19.25 % of the new developed polyurethane (PU) memory foam in sock of sample 2 and 21.09 for sample 3 is obtained within the standard range in SATRA test method, and greater than that of existed PU foam in sock. The failing of the test result below standard requirement leads the product strength somewhat poor. In contrary, if this property is above standard it will be less flexible and comfort so, it should be between standard requirements. The only difference between in sample 2 and 3 is due to using of different amount of surfactant (castor oil). Therefore, the new product in this research shows the product have fulfilled the standard requirement and are acceptable

Thickness:

The recipe of the chemicals/materials including the new surfactant material, castor oil and tap water is formulated based on SATRA standards and Amaga foam factory in Ethiopia materials to produce 11mm foam in sock thickness and then manufactured it. After developing the products sample 2 and 3 the mean value of both sample thickness showed uniformity of the developed in sock. Therefore, as the new research result shows it is possible to manufacture these products with uniform thickness.

Compression set:

elastic properties of the in sock was conducted for both sample 2 and 3 each and all of the test resulted for sample 2 in average is 3.82%, which is within standard requirement. In case of sample 2 is 4.2% which is also between the standard but its value is greater than that of sample 1. The commercial /existed normal foam in sock/ shoe insert value is 6.1, which is not fit with standard requirements, this shows that

just commercial in sock is not good for diabetic foot ulcer patients foot ulcer treatment due to lower elastic property than that of standards. This leads the product to have lower comfort particularly in this property because orthopedic shoe appliance need to be more flexible and comfort for foot ulcer patients and Products with good compression set has good comfort.

Abrasion test:

The purpose of testing of this property is to know its resistance to abrasion because during wearing the in sock will rub between our feet and the shoe sole/insole, so it needs to have very good Abrasion resistance. To know this property, the experimental test in abrasion resistance of normal PU Foam and that of the new developed foam in sock were conducted. From these as result shown the PU memory foam in sock abrasion resistance resulted is very good than that commercial foam value because it has less amount of weight loses due to abrasion than that of normal PU foam. This implies that the newly developed memory foam in sock will resist any forces that rub it by that it will have longer life span than commercial PU foam/in sock however, sample 3 is lower than that of sample 2 because in sample one is low density due to lower amount of surfactant (castor oil) use.

Pressure redistribution test of the shoe insert

After the pressure reduction and distribution properties of the developed shoe insert was measured at leather industry development institute (LIDI) Addis Ababa, Ethiopia. The ethyl vinyl acetate, (EVA) and the new developed memory foam shoe insert carbon test results is presented in Figure .

The contact area (points) of carbon on in sock were almost the same but, the picture of test results of memory foam shoe insert slightly greater than that of EVA shoe insert, this implies that, our foot contact to shoe insert during wear is also higher. Therefore, if the contact area is higher it reduces our body pressure and redistribute it to the ground by this it reduces foot ulcer pain. Pressure from walking can make an infection worse and an ulcer expand. For people who are overweight, extra pressure may be the cause of ongoing foot pain but by using /wearing orthopedic footwear with memory foam cushion in sock/ insert our body pressure during walking can be redistribute evenly and the development of ongoing foot pain plus its ulceration development retards because in socks can increase contact areas of our feet and then decrease our pressure.

Conclusion

Foot ulcer is an open sore mainly on the bottom of our feet caused by diabetic disease. Therapeutic shoe with appliance (in socks) like polyurethane (PU) memory foam in sock plays a great role in retarding foot ulcer. The in sock which was prepared by using materials used for preparing PU memory foam mattress with 5g, 9.5 g and 10.36g of castor oil surfactant, the third one was showed better comfort properties and the first one was unable to be foam but it remains as a thick liquid. In this research the new in sock was

developed, at low cost by including less cost and locally available surfactant materials (castor oil) instead of costly silicon surfactant and tap water instead of distilled water. In the field test at Adina's hospital, Bahir Dar Ethiopia implies a very good comfort, and very good pressure reduction ability

Therefore, from this study the newly developed in sock showed good futurity for foot ulcer patients and solve limited access problem by affordable price through manufacturing it locally.

Abbreviations

EVA: ethyl vinyl acetate; PU: Polyurethane; P.L.C: private limited company; SATRA: South African Telecommunications Regulatory Authority; LIDI: leather Industry development Institute; TDI: toluene Di – Isocyanate; MM: millimeter/CC: gram per centimeter cubic ;G/CM3: gram per centimeter; G/L: gram per liter; HT; specific code polyurethane

Declarations

Acknowledgment

Our sincere gratefulness goes to the staff of Ethiopian Institute of Textile and Fashion Technology, Lather Technology Bahir University for their help and the institute for the financial funding, as well as providing access to all necessary materials for the successful completion of the research.

Author's contribution

Awoke Fenta Wodag: Conceptualization the idea, Methodology, Data analysis, writing the first draft preparation, Visualization, Investigation, Final reviewing, and editing.

Adane Adugna Ayalew: Reviewing the manuscript formats, paper fonts and structure

Funding

This work was supported by research and Postgraduate graduated office, Ethiopian Institute of Textile and Fashion Technology Bahir Dar, University

Availability of data and materials

All the datasets are available from corresponding author if required.

Ethics approval and consent to participate.

All the participants, from Adinas Hospital patients in Bahir Dar, Ethiopia, are asked and had showed their voluntariness' (consent) prior to their participation and then the products are checked on them.

Consent for publication

Not applicable.

Conflict of interest

It is declared that they have not conflict of interest.

Author details

¹ Department of leather engineering, Ethiopian Institute of Textile and Fashion Technology Bahir Dar, University, Ethiopia.

²Department of Chemical Engineering, Bahir Dar Institute of Technology, Bahir Dar, University, Ethiopia.

References

1. Armstrong DG, Lavery LA; Diabetic Foot Study Consortium. Negative pressure wound therapy after partial diabetic foot amputation: a multicentre, randomised controlled trial. *Lancet*. 2005.
2. Deribe, B, Woldemichae, K, Nemera, G. 2013. Prevalence and Factors Influencing Diabetic Foot Ulcer among Diabetic Patients Attending Arbaminch Hospital, South Ethiopia. *Journal of Diabetes and Metabolism*. 5:1-6.
3. Eginton M. T., Brown K. R., Seabrook G. R., Towne J. B., Cambria R. A. A. 2003. Prospective randomized evaluation of negative-pressure wound dressings for diabetic foot wounds. *Ann Vasc Surg*. 17:1-9
4. Gebre, M.W. (2013). Diabetes mellitus and associated diseases from Ethiopian perspective Systematic review. *Ethiop. J. Health Dev.*, 27:25-252.
5. Gebrekidan, G. F., Gezahagn, T. G. 2016. PU Memory Foam for Application as Insole in Therapeutic Footwear for Patients with Diabetes. *International J. Engineering Science and Computing*. 6:1-2.
6. Gnanasundaram, S, Durairaj, D, Gopalakrishna, G, Das, B. 2013. PU viscoelastic memory foam for application as cushion insole/insock in shoe. *Proceedings of the Eleventh Footwear Biomechanics Symposium*.5:522-523.
7. Jeon, C. Y., Harries, A. D., Baker, M. A., Hart, J. E.(2010). Bi-directional screening for tuberculosis and diabetes: a systematic review. *International J. of health scien*.15:1365-3156

8. Khan H, Khan Z, Jamal, Din, Rehman S, Khan B. 2011. Factors contributing to the development of diabetic foot ulcers and role of health literacy. *Bibliomed.* 36:34-37.
9. Kumar, J.V., Sathyaseelan, Jeyakumar.2016. Foam Dressings in the Topical Management of Diabetic Foot. *J. of Dental and Medic. Sciences.*15:32-35.
10. Saraswathy G, Gautham G, Das BN, Ganga R, Pal S. 2009. *Polymer Plastics Technology and Engineering,* 48:239 -250.
11. Tesfatsion, M., Yifter, H. Teklu, L. 2015. Risk factors assessment of diabetic foot ulcer using the sixty seconds screening tool: a hospital based cross-sectional study at Tikur Anbessa specialized hospital. *Ethiop Med. J.* 2:45-49.
12. Worku D, Hamza L, Woldemichael K. 2010. Pattern of diabetic complications at Jimma University Specialized Hospital, Southwest Ethiopia. *Ethiop. J. Health Sci.* 20:33-3.
13. Yemane T, Belachew T, Asaminew B, Befekadu O. 2007. Type II diabetes mellitus in Jimma Town, South West Ethiopia. *Eth J Health Sci.* 17: 107-114.
14. Zhang, P, L. u., J., Jing, Y., Tang, S., Zhu, D., Bi, Y. 2017. Global epidemiology of diabetic foot ulceration: a systematic review and meta-analysis. *Annals of Medicine.* 49: 106-116.

Figures

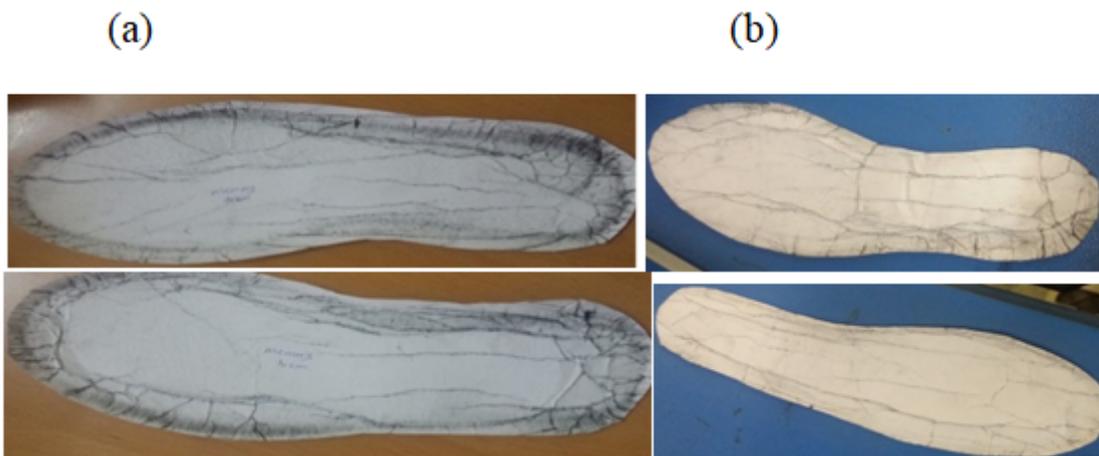


Figure 1

Comparison of (a) carbon copy test result of EVA and (b) Memory foam shoe insert