

# On The Stability of Triangular Janus MoSSe Quantum-Dots: Shape and Size Effects

J. I. Paez-Ornelas (✉ [josepaez@cicese.edu.mx](mailto:josepaez@cicese.edu.mx))

Center for Scientific Research and Higher Education at Ensenada

R. Ponce-Perez

National Autonomous University of Mexico

H. N. Fernández-Escamilla

National Autonomous University of Mexico

D. M. Hoat

Duy Tan University

E. A. Murillo-Bracamontes

National Autonomous University of Mexico

Ma Guadalupe Moreno Armenta

National Autonomous University of Mexico

Donald H. Galván

National Autonomous University of Mexico

J. Guerrero-Sánchez

National Autonomous University of Mexico

---

## Research Article

**Keywords:** triangular, TMDs, dichalcogenide, MoSSe

**Posted Date:** August 26th, 2021

**DOI:** <https://doi.org/10.21203/rs.3.rs-841645/v1>

**License:**   This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

---

# On the stability of triangular Janus MoSSe quantum-dots: shape and size effects

J.I. Paez-Ornelas<sup>1,2,\*</sup>, R. Ponce-Perez<sup>2</sup>, H. N. Fernández-Escamilla<sup>2</sup>, D.M. Hoat<sup>3,4</sup>, E.A. Murillo-Bracamontes<sup>2</sup>, Ma Guadalupe Moreno Armenta<sup>2</sup>, Donald H. Galván<sup>2</sup>, and J. Guerrero-Sánchez<sup>2,\*</sup>

<sup>1</sup>Centro de Investigación Científica de Educación Superior de Ensenada, Ensenada Baja California, 22800, México

<sup>2</sup>Centro de Nanociencias y Nanotecnología, Universidad Nacional Autónoma de México, Apartado Postal 14, Ensenada Baja California, Código Postal 22800, México

<sup>3</sup>Institute of Theoretical and Applied Research, Duy Tan University, Hanoi 100000, Viet Nam

<sup>4</sup>Faculty of Natural Sciences, Duy Tan University, Da Nang 550000, Viet Nam

\*josepaez@cicese.edu.mx, \*guerrero@ens.cnyn.unam.mx

## ABSTRACT

Asymmetric Janus transition metal dichalcogenide MoSSe is a promising catalytic material due to the intrinsic in-plane dipole of its opposite faces. The atomic description of the structures observed by experimental techniques is relevant to tune and optimize the reaction processes on its surfaces. Furthermore, the experimentally observed triangular morphologies in MoSSe suggest that an analysis of the chemical environment of its edges is vital to understand its reactivity. Here we analyze the size-shape stability among different triangular structures -quantum dots- proposed from the ideal S(-1010) and Mo(10-10) terminations. Our stability analysis evidenced that the S-Se termination is more stable than Mo; moreover, as the size of the quantum dot increases, its stability increases as well. Besides, a trend is observed, with the appearance of elongated Mo-S/Se bonds at symmetric positions of the edges. Tersoff-Hamann scanning tunneling microscopy images for both faces of the stablest models are presented. Electrostatic potential isosurfaces denote that the basal plane on the S face of both configurations remains the region with more electron density concentration. These results point toward the differentiated activity over both faces. Finally, our study denotes the exact atomic arrangement on the edges of MoSSe quantum dots corresponding with the formation of S/Se dimmers who decorates the edges and their role along with the faces as catalytic sites.

## Introduction

Transition metal dichalcogenides (TMDs) are nowadays among the most investigated and characterized materials in solid-state physics. The amply different features shown by the bulk and the monolayer (ML) have led to a broad scope of applications in diverse areas such as nanoelectronics<sup>1,2</sup>, energy storage<sup>3</sup>, spintronics<sup>4,5</sup>, and catalysis<sup>6</sup>.

TMDs have a general formula  $MX_2$  where M is a transition metal, and X represents a chalcogen element. The bulk TMDs are made up of stacked laminar structures through van der Waals-type interactions where each layer is composed of three species (X-M-X) -forming a single triple layer-. This fact has allowed ML isolation by cleavage or mechanical exfoliation<sup>7</sup>. Moreover, interesting properties emerge during the shift from bulk to ML phases: transitioning from indirect to direct bandgap<sup>8</sup>, spin-valley coupling<sup>9</sup>, and good carrier mobility at room temperature, renewing the interest in the 2D layered TMD family<sup>10</sup>.

In TMDs, the transition metal coordination with the chalcogen elements and the stacking order can lead to four differentiated phases: 1T, and distorted 1T' with octahedral coordination, plus 2H and 3R with trigonal prismatic coordination<sup>11</sup>. However, in the ML, the dominant phases are 1T and 1H -a single triple-layer from 2H bulk-<sup>12</sup>. These structures have been the focus of intense research as they present intrinsic in-plane asymmetry<sup>13</sup>. The asymmetry is vital since compared to other laminar materials such as graphene, it leads to obtaining direct bandgap materials without introducing external fields or layer stacking<sup>14</sup>. Their electronic behavior has been a key factor to be considered active participants in catalytic reactions<sup>15</sup>.

The performance of TMDs ML as catalytic materials has been demonstrated during the last century with the use of  $MoS_2$  to catalyze several petroleum refinery reactions as hydrodesulfurization (HDS) hydrogenation (HYD), and metals remotion. However, the details of its atomic structure were unknown until the Besenbacher group obtained the first STM images<sup>16</sup>. Their study concluded that the ML of  $MoS_2$  stabilizes as triangular quantum dots of varied sizes under sulfiding conditions. So far, many combinations of TMDs have been investigated in the hunt for materials with enhanced catalytic activity.

Recently, an additional degree of freedom in TMD ML causing out-of-plane asymmetry has been achieved by a structural modification to form the so-called Janus ML<sup>17</sup>. This family has the general formula XMY and can be obtained by the substitution

of one chalcogen atom of the single triple-layer<sup>18</sup>. Since X and Y are different chalcogen elements, the surfaces are expected to possess distinctive electronic behavior and different catalytic activity.

Although different Janus structures have been theoretically predicted as stable<sup>19–21</sup>, only a few reports of its experimental synthesis exist. The groups of Li and Jun have reported two different procedures to synthesize the 1H MoSSe Janus ML<sup>22,23</sup>.

In the methodology presented by Li<sup>22</sup>, a  $MoSe_2$  ML template was grown by CVD, then a direct exchange of the top layer was performed by controlled substitution reaction of S in the  $MoSe_2$  ML to form MoSSe. On the other hand, a  $MoS_2$  ML template was used in Jun's methodology. The  $MoS_2$  ML was exposed to  $H_2$  plasma to remove the top S layer and form MoSH. Finally, a selenization of the sample is reached with thermal vaporization of Se powders to obtain MoSSe. The structures obtained were analyzed by STM. Their morphology is consistent with triangular quantum dots of diverse dimensions as also observed in  $MoS_2$  STM investigations<sup>16,24</sup>. However, there is not enough structural information to build an exact atomic model that allows studies on the edge terminations of these structures, their stability, and their role as catalytic models<sup>25</sup>. Further analysis is needed to provide further insight into morphology and border-termination; such atomic-scale description may help understand and improve materials with enhanced catalytic activity.

This article discusses the atomic arrangement observed in Li and Jun's experimental pioneering work to synthesize 1H MoSSe Janus ML. We study the stability by first principles-thermodynamics of four triangular structures consistent with the experimentally observed morphology, which may have Mo or S-Se termination. Our results denote that the configurations with S/Se dimers on edge remain the most stable models. Furthermore, from a structural analysis for triangles of different sizes, a trend is observed by the appearance of elongated Mo-S/Se bonds in symmetric positions of the edge for large triangles. Tersoff-Hamann scanning tunneling microscopy simulations of the stablest model are presented. Electrostatic potential isosurfaces point that the basal plane on the S face of both configurations remains the region with more electron density concentration. Their role hints at the preferential activity of the faces. Finally, our study denotes the exact atomic arrangement on the edges of MoSSe quantum dots corresponding with S/Se dimers that decorates the edges and their role -along with the faces- as catalytic sites.

## Results

In this work, different triangular structures obtained via the ML breaking in the low index edge termination were proposed to study their stability as a function of size and edge termination.

First, the hexagonal 1H-MoSSe ML unit cell was optimized and used as a template from which the triangular structures were obtained. The calculated lattice parameter was  $a_0 = 3.23 \text{ \AA}$  in good agreement with the experimental value of  $3.22 \text{ \AA}$ <sup>22</sup>, the Mo-S/Se bond distances were 2.41 and 2.53  $\text{\AA}$  respectively, whereas the angles  $\angle MoSMo$ ,  $\angle SMOSe$ ,  $\angle MoSeMo$  had the values:  $83.98^\circ$ ,  $81.92^\circ$ , and  $79.35^\circ$ .

As mentioned in the methods section, the reference set for this study has been the  $MoS_2^{Bulk}$ ; therefore, we calculated the formation enthalpy ( $\Delta H_f$ ) for this system, obtaining a value of 2.58 eV in accordance with previous theoretical calculations<sup>26,27</sup>, and very close to the experimental value of 2.86 eV<sup>28</sup>.


### 0.1 Structural configurations

The triangular structures were built based on the Mo ( $10\bar{1}0$ ) or S/Se ( $\bar{1}010$ ) terminations from the MoSSe ML. Since both terminations present different exposure of the border atom (see Fig. 1a-d), four different structures can emerge: two with S-Se dimers as the protruding species labeled as C1 and C2 where each Mo atom is six-fold coordinated, plus other two configurations with protruding Mo atoms labeled as C3 and C4 where the S and Se atoms of each face are three-fold coordinated with the closest Mo atoms. In these configurations, the coordination of the species except for the border atoms resembles that of the ML.

Note that the ideal structures (see the upper part on Figure 1) contain the same number of Mo atoms per edge; this number is employed to set the size of the system under study. Therefore, we constructed models for the four configurations containing  $n$  Mo atoms per edge where  $n$  can take values ranging from 4 to 10. Depending on the configuration, these systems are labeled as CX( $n$ ).

In C1, the ( $10\bar{1}0$ ) termination contains S-Se protruding dimers where each dimer is bonded with a single Mo atom over the edge in a triangular area enclosed by the Mo atoms (see Figure 1a). After structural relaxation, this configuration remains less distorted; note that the S-Se dimers over the edge tend to stabilize the deformation of the structure. The S-Se bond distance is 2.13  $\text{\AA}$  in the inner part of the edges and 2.17  $\text{\AA}$  on the corners.

Subsequently, C2 obtained from the ( $\bar{1}010$ ) termination is characterized by the formation of a zig-zag edge where the S-Se dimers protrude and are bonded with two adjacent Mo atoms (see Figure 1b). Note that after relaxation, in each corner over the Se side of the Janus structure, Se dimers tend to appear over the Mo atom of the corner with bond distance ranging between 2.44-2.46  $\text{\AA}$ . The side view shows that this structure tends to curve towards the face of S atoms. This behavior becomes more marked as the size of the system increases.

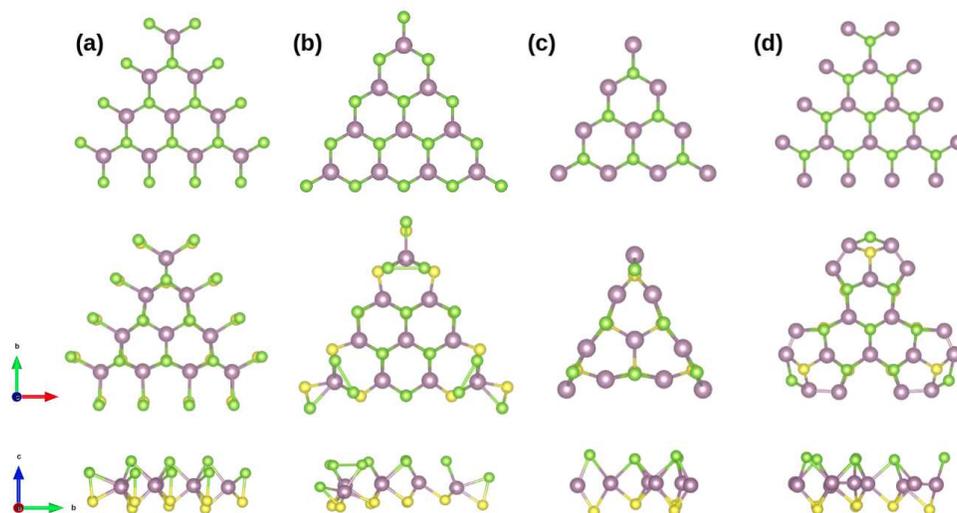

**Figure 1.** 1H-MoSSe quantum-dots obtained by the breaking of the ML in the low symmetry indexes direction. (a) C1(4) from the  $(10\bar{1}0)$  termination depicts Mo atoms in six-fold coordination where each Mo over the edge is bonded to a protruding S/Se dimer. (b) C2(4) from the  $(\bar{1}010)$  termination, where the Mo atoms are also six-fold coordination. However, the Mo atoms from each edge are bonded with two S/Se dimmers forming a zig-zag pattern. (c) C3(4) where S/Se atoms are three-fold coordinates with the Mo atoms forming a zig-zag edge with Mo exposed, and (d) C4(4) obtained from C1 exchanging Mo atoms with S/Se dimmers. S, Se, and Mo atoms are depicted as yellow, green and violet spheres.

The following configurations are characterized by the exposure of Mo atoms and indeed are those that present a greater structural distortion (see the lower part on Fig. 1c). C3 corresponds to a  $(10\bar{1}0)$  fully Mo terminated; note that this configuration corresponds to C1 with the remotion of the S/Se dimers over the edge. After structural relaxation, the Mo atoms on the edges tend to rearrange themselves to dominate the M-Mo interaction; their displacement towards the center evidences this behavior. Finally, an additional configuration, C4, can be constructed by exchanging positions between S-Se dimers and Mo atoms from C2. This system is, in fact, the one that presents a greater atomic rearrangement (see Figure 1d).


The edge terminations of these systems have been previously considered in detail only for the predecessor structure  $MoS_2$ . The Besenbacher group confirmed by STM images that the nanoparticles had triangular shapes with S terminations providing a new picture of reactivity in this class of structures<sup>16</sup>. Moreover, based on the fact that triangular morphologies suggest that one of the edge terminations must be more stable, other theoretical works have been devoted to determining the exact atomic arrangement over a wide range of sulfiding conditions<sup>26</sup>. The results presented through DFT by Joo et al.<sup>26</sup>, were consistent with the assumption of Besenbacher, where the edge protrusion of the triangular structures should be associated with S atoms whose height was shifted by a half lattice constant compared with the truncated position of the ML. It is important to mention that such a difference in height for the MoS<sub>2</sub> structure was not identified through atomic force microscopy (AFM) measurements; in fact, the height was consistent with that of the monolayer, suggesting that the presence of two atomic species modifies the arrangement of the edges -this is Se and S-<sup>22</sup>.

Nevertheless, no conclusion about the termination and stability of the MoS<sub>2</sub> system has been developed. Therefore, we present a stability analysis that compares the previously described structures and the role of the simple Mo or combined S/Se termination.

## 0.2 Stability

Next, once we explain the triangular configurations that can be obtained from the MoS<sub>2</sub> ML, we have employed the surface formation energy formalism to analyze their formation energy accordingly to equation 5 as for systems of the same size (n Mo per edge) the number of atoms is different.

The calculated SFE of the proposed terminations: C1(n), C2(n), C3(n) and, C4(n) as a function of their size is depicted in Figure 2. -The size of the different configuration range between 4 to 10 Mo per edge-. The  $MoS_2^{Bulk}$  seated as the reference in our thermodynamic analysis is represented by a green dotted line. Since we are working with systems coming from the ML, we have introduced two additional references that appear slightly over the  $MoS_2^{Bulk}$ : this is the  $MoS_2$  ML followed by the MoS<sub>2</sub> ML. These systems are represented by dotted orange and black lines, respectively. Above these values, the systems under study are shown; note that as the values move away from the reference, their stability decreases; however, as these values tend to get

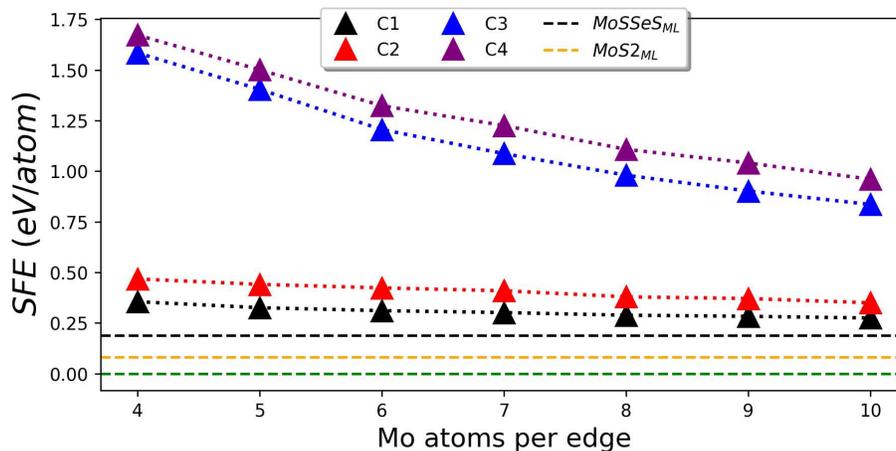

**Figure 2.** SFE for the four proposed triangular MoSSe quantum dots. C1, C2, C3, and C4 are represented by red, blue, black, and purple triangles. The  $MoS_2^{Bulk}$  is set as the reference and is depicted as a dotted green line. Over the reference the  $MoS_2$ , and MoSSe MLs are represented by an orange and black dotted line.

closer to the reference, their stability indicates that their formation is likely to appear.

Our findings show that the S/Se terminated systems: C1(n) and C2(n) are more stable than Mo terminated: C3(n) and C4(n). Moreover, as the size of the system increases, a trend is observed where all systems tend to stabilize approaching the  $MoSSe$  ML. Note that Mo terminated configurations present a more marked change in energy evidenced by an abrupt drop in their slopes. This behavior has been described for triangular structures and can be correlated with two perspectives associated with the number of unsaturated atoms over the edge<sup>26</sup>. First, as the system size increases, the ratio between the number of S/Se and Mo atoms increases to reach the bulk value. The second perspective considers the opposite trend. The ratio between the atoms over the edge and the total number of atoms decreases, indicating that the number of not fully coordinated Mo atoms over the edge is reduced. Therefore, an interplay related to an increment in the system size is evident to gain stability.

On the other hand, for the S/Se terminated systems, the stability trend is uniform, suggesting that structures throughout the full-size range have the same probability of appearing under experimental conditions. Note that C1(n) and C2(n) have a slight energy difference so that both terminations could coexist in all the ranges of size under experimental conditions<sup>24</sup>.

The size distribution of these structures has been examined before in  $MoS_2$  quantum dots<sup>24,29</sup>. The analysis unveiled that after close inspection of the size distribution of triangles in STM images, two main groups of distribution could be set: for the larger triangles, it was determined that predominant size was related with the number of Mo atoms per edge: with  $n=8, 10, 12$ , and  $14$ , as the size of the system increased the species count decreased. In contrast, in smaller triangles, the trend was opposite, where the highest abundance corresponded to structures with  $n=4$  followed by  $n=6$  Mo per edge.


This analysis of the size of the system is vital since the dimensionality effect in the electronic properties of confined systems has been commonly established, resulting in differentiated and even outstanding catalytic activity in several reactions as hydrogen-evolution reaction (HER) or oxygen-reduction reaction (ORR) as a function not only of edge termination but also of the size<sup>26,29</sup>.

### 0.3 Geometrical distortion

Motivated by the differentiated rearrangement over both faces of the Janus structures, we have performed a detailed bond distances study, both in the center of the structures and on the edges. Besides, as the system size increases, some edge regions present elongated Mo-S/Se bonds or the formation of new S/Se dimers. This fact must be monitored to understand the sites where S or Se could be shed during reactions catalyzed by these structures.

To show the bond distribution present in these structures, we have selected two model systems containing the broader bond distribution. The selected systems C1(10) and C2(10) are presented in Figure 3 where a color code has been applied to differentiate between bond ranges.

For both configurations, a figure showing the distribution on both faces is presented, the individual contributions of the S or Se faces are shown on the right-hand side. Note that according to the color code for C1(10) (see Figure 3a), the shorter bonds correspond with the S-Se dimers that decor the edges of the structure; these bonds range between 2.12-2.16 Å. Analyzing the S side of the Janus structure, the next bond in yellow corresponds to the Mo atom from the vertex and the S located towards the center of the structure. The length of this bond is highly uniform, with a value of 2.35 Å. The following bond in red color is associated with the Mo-S interaction ranging between 2.67-2.42 Å; the amply distribution presented by this bond is consistent

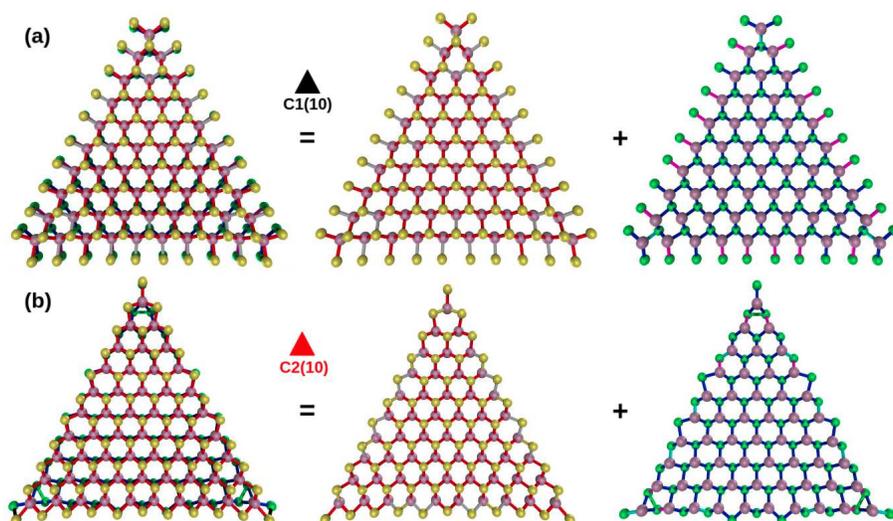

**Figure 3.** Bond length distribution of the stablest S/Se terminations. The image at the left is formed by the combination of the adjacent images where each face is shown (a) C1(10), and (b) C2(10). S, Se, and Mo atoms are depicted as yellow, green and violet spheres.

with the fact that many S atoms from the edges undergo a structural rearrangement that moves it away from the ideal value of 2.41 of the ML. Finally, the more elongated bonds with values among 2.42-2.45 Å are depicted in gray.

Now, the Se side shows contracted Mo-Se bond with a value of 2.48 Å in cyan color. This bond is correlated with the Mo atom from the vertex and the adjacent Se atom that points toward the center. Next, the wider bond distribution is shown in blue, with values that range between 2.49-2.58 Å. Once again, using the previous analysis, it can be determined that this distribution corresponds to the structural rearrangement of the Se atoms at the edge. Finally, the broader bond with values between 2.58-2.61 Å is shown in magenta. Its main contribution is in the center of the edges and on symmetrical positions contiguous to the tips of the structure.


In C2(10), a wider variety of bond distances can be observed. As mention before, the concavity of the C2(n) is greater than in C1(c), therefore as the structure tends to bend, the bonds elongation(contraction) of the Se(S) is more evident as the system size increases. In this type of termination, two types of dimmers appear in the color code scheme (see Figure 3b): S-Se in black, that can be observed at each vertex, but also two additional dimmers are formed over each edge, these dimmers are located next to the S-Se at the edge center with a bond distance of 2.21-2.22 Å. The other class of dimmers in green is Se-Se, located over each tip with a distance of 2.43-2.45 Å. It is relevant to mention that for systems with  $n < 9$  the appearance of a single S-Se dimer is observed on edge, while for  $n = 10$  an additional dimer is formed.

From the S side, the next bond in yellow is the Mo-S with a value of 2.25-2.29 Å; note that their location corresponds to the Mo of the vertex, and the concavity of the structure forms a pair of these on the fourth and fifth Mo atom over each edge. The rearrangement of the electronic distribution on the highlighted Mo atoms creates, as a related consequence, the appearance of an elongated Mo-S bond; this bond depicted in gray has the longest value of 2.45-2.46 Å. This last type of elongated bond is observed only in structures with  $n > 7$ ; for smaller triangles, such elongation does not exist. Finally, the remaining Mo-S bonds are displayed in red; the distribution reflects the noticeable structural changes over the edges; these bonds values are in the 2.30-2.42 Å range.

Concerning the Se side, the first kind of bond that appears is the Se dimer in green described previously. Next in length, the Mo-Se interaction can be classified into three groups; the smaller distance with a value of 2.45-2.48 Å is shown in cyan, located at the vertex of the structure and over the third and fifth Mo atom. The next bond in blue corresponds to bonds in the 2.49-2.6 Å range; as can be observed, this value oscillates around the ideal Mo-Se value of 2.53 Å. Finally, the broader bond of 2.61-2.65 Å is shown in magenta.

A bond length analysis, as reported before, has been applied to the S/Se terminated configurations C1 and C2 to study the morphological differences over the edges and the center of the structures; these results are summarized in Figure 4. The configurations shown from top to bottom correspond with the system size starting from  $n=4$  to 10. The ideal values of the Mo-S(Se) bonds of 2.41(2.53)Å are represented by a vertical dotted line in red(blue). The color code employed in the previous section is kept to show the number of bonds against the bond distance.

The S-Se dimmers represented by black diamonds are located in the left part of both graphs. For C1(n) (see Figure 4a), as

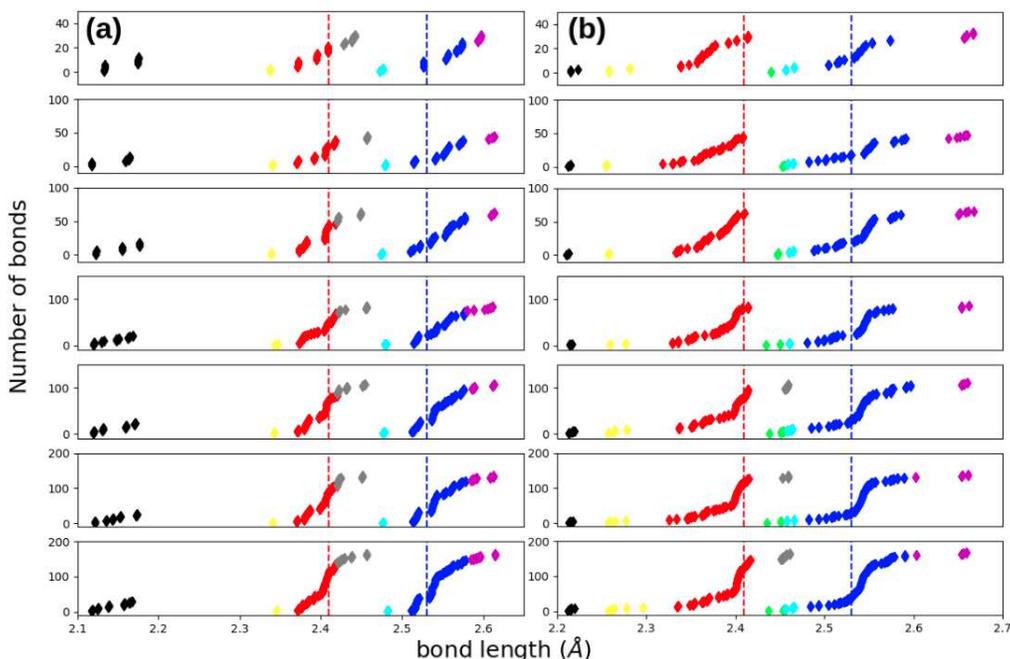

**Figure 4.** Bond distance distribution for the stablest S/Se terminated configurations. (a) C1( $n$ ) with  $n=4-10$  from top to bottom, and (b) C2( $n$ ) with  $n=4-10$  from top to bottom.


the size of the system increases, the formation of new dimers around the structure is evident; the bond measures between these are varied since they are those that support the structural rearrangement towards the edges. In contrast, C2( $n$ ) (see Figure 4b) present a uniform distribution since the S-Se dimer is only located at the corners, nevertheless as mentioned, for systems with  $n > 7$ , the appearance of new points can be perceived, these values are similar in length. The S-Mo bond of the tips in yellow is again uniform for C1( $n$ ) since it is associated exclusively with the Mo of the vertex. In contrast, for C2( $n$ ), the system size causes the appearance of new contracted bonds related to the S-Mo bond at the edges; again, as the system increase in size, a wider distribution should be associated. This more evident rearrangement between the two structures is also supported by the ideal reorganization of the Mo-S bond; as can be seen in general, C1( $n$ ) remains less distorted than C2( $n$ ) following the bond distribution in red. The elongated Mo-S bond in gray remains in all the range of Mo atoms per edge for C1( $n$ ). Still, a complete trend is observed on C2(2). The presence of these elongated bonds emerges exclusively when  $n > 7$ . The Se-Se dimmers formation is exclusively from C2( $n$ ) and appears in green. In cyan, the number of shorter Se-Mo bonds remains unaffected for C1( $n$ ) as their formation is only through the Mo of the tip. For C2( $n$ ), the same behavior is displayed, suggesting that the contracted bonds over the edge are present in all the range of sizes. Finally, the bond distribution of the Mo-Se interaction in blue is broader again for C2( $n$ ) if compared with C1( $n$ ) as an effect of the more severe rearrangement. The longest Mo-Se bond in magenta is again symmetrical and unaffected by the increase in size.

The analysis set brings insights into a crucial reaction mechanism that this kind of structure should promote; intriguingly, the bond distributions showed interesting structural properties -that emerge in the atomic regime- and are significantly modified as the size of the system is altered. This observation hints that the catalytic activity is conditioned on the edge termination and by the size. The study of the role of dimensionality and size-dependent in  $MoS_2$  quantum-dots has demonstrated that properties as sulfur bonding strength or hydrogen dissociation are both: size and edge dependent. Besides, through the analysis of STM images, it has been shown that small structures with  $n = 4$  reveal the formation of spontaneous sulfur vacancies at the edges; an opposite trend has been observed for larger triangles where the vacancies appeared over the entire edge<sup>24</sup>.


#### 0.4 TH-STM analysis

This section focuses on analyzing the morphology of the C1( $n$ ) and C2( $n$ ) employing the Tersoff-Hamann approximation where the detected current is proportional to the local density of states at the Fermi level where the tip is positioned<sup>30</sup>. The simulated atomically resolved STM images bring insight into the different features shown on both sides of the structure. Figure 5(a) shows simulated images for C1( $n$ ) obtained via constant current utilizing a tunneling current of  $5 \times 10^{-5}$  a.u. and in constant height mode with a separation distance from the surface of  $3.5 \text{ \AA}$ .

When using images in constant height mode (upper section in S/Se faces see Figure 5(a,b)), the curvature of the structures

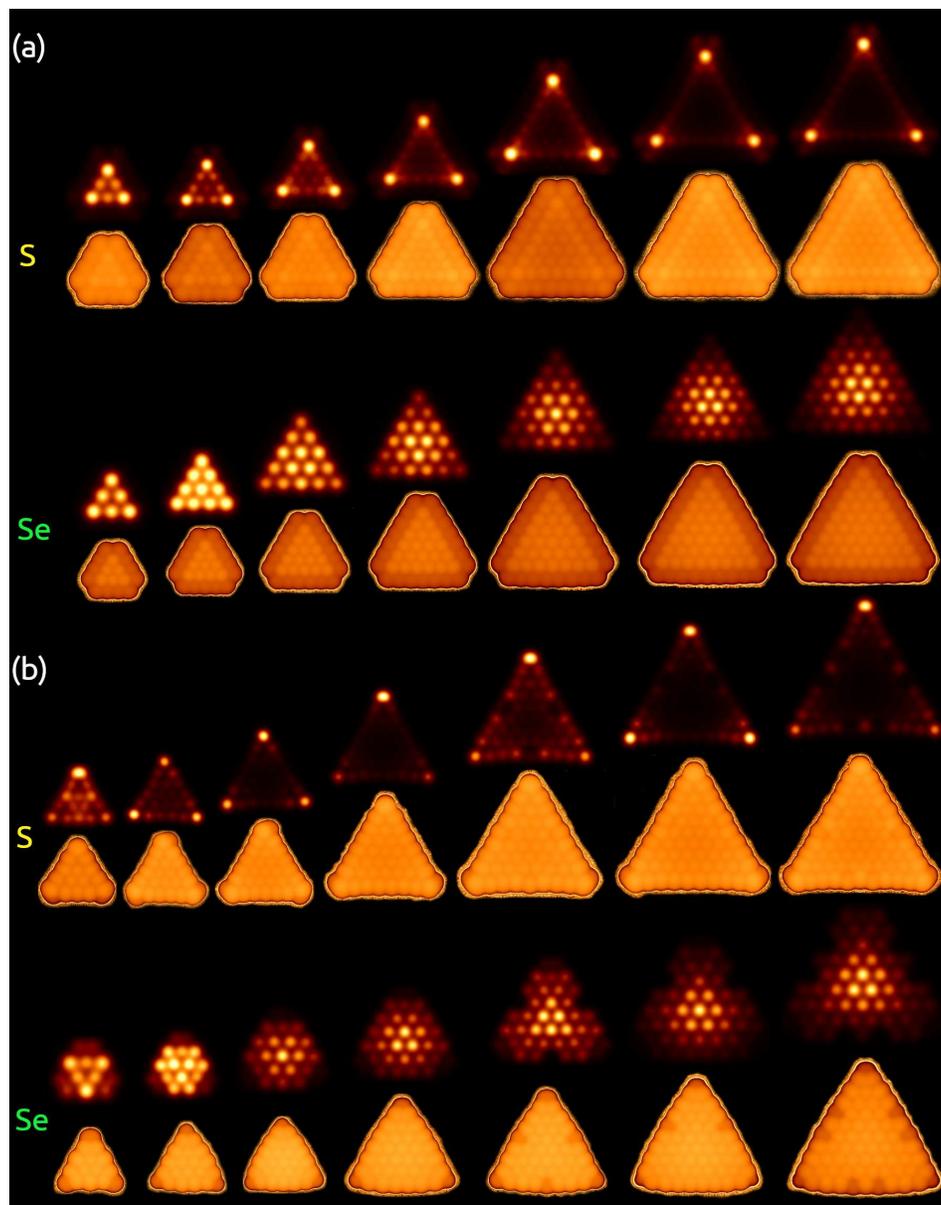

**Figure 5.** Tersoff-Hamman STM images that unravels the atomic scale details of the C1(n), and C2(n) with  $n=4-10$ . The images presented were obtained by constant height, and constant current modes over both faces of the Janus MoSSe quantum-dots. (a) C1(n), and (b) C2(n)

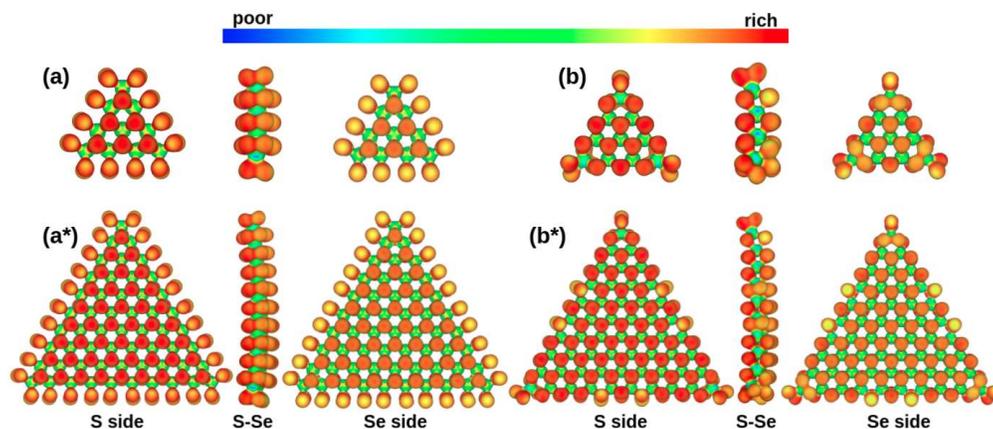

**Figure 6.** Electrostatic potential isosurface used to visualize electron rich areas on the more stable structures. (a) C1(4), (a\*) C1(10), (b) C2(4), (b\*) C2(10).

can be observed due to a greater brightness depending on the side that is analyzed. This contribution is greater at the vertex for the S side, and its appearance is evident from the smaller triangle. For the Se side, the brightness in the central region of the triangle is startled. When  $n = 4$ , the brightness observed over the center of the triangle seems to emulate the metallic edge state observed in the adjacent row of the outermost edge on the  $MoS_2$  system<sup>24</sup>. However, with  $n > 4$ , the contribution becomes marked in the center with the highest contribution coming from the Se atom and remains as the size increases.

For the constant current mode, the images were obtained to decrease curvature's effect in identifying potential reaction sites (see the lower section in S/Se faces on Figure 5(a,b)). Our analysis reveals that the significant contribution arises from the basal plane of both faces in both configurations. Nevertheless, note that for C1, the S side presents a significant contribution coming from the basal plane with a shiny region around the edges; S atoms shifted 0.1 Å in height generates this signal. On the other hand, for the Se side, it can be seen that excluding the Se atoms that decor the edge forming S-Se dimmers, a triangular structure emerges that appears to be framed by the border and whose height is greater than the border. The brim contribution of this inner triangle is higher than the edge for all the triangles distribution. These sections are consistent with our previous analysis of geometrical distortion.

The evidence presented is a clear indication that the curvature of the structure is generated towards the side of the sulfur face in both systems. Moreover, the brim regions bring insight into the differential catalytic activity correlated with the regions of higher electron density on both faces. However, an analysis of the charge distribution is vital to assess this critical behavior.

### 0.5 Electrostatic Potential isosurface

Electrostatic potential isosurfaces (EPI) were employed to visualize in real space regions with charge concentration as potential reactive points for the interaction of the quantum dots with target molecules in catalytic reactions. For the representation of EPI, we have used an 0.05 a.u. isovalue and an RGB color code to account for charge accumulation areas in red and charge depletion in blue. The EPI obtained shows a difference in the accumulation of charge on both faces of the Janus structures (see Figure 6).

In general, the side that contains a more electronegative element -as in this case S-, accumulates more charge than the Se face and is denoted by an increment in the red color of the face. Note that both areas account for electron-rich regions compared to the Mo atom at the center of the three layers, whose role is denoted as an electron donor. It is important to mention that for C1(n), the same electronic behavior is observed for both system sizes. Note that the smaller triangles -on both faces- enclosed by the outermost Mo atom are more electron abides than the edges. The differentiated accumulations of electrons observed at the edge can be correlated because S-Se dimmers over the edge are bound to one Mo against S/Se atoms towards the center bounded with three Mo each; therefore, these regions are more electron abides.

For C2(n) (see Figure 6), the smaller structure presents a uniform electron distribution over the faces; the exceptions are the S-Se dimmers at the vertex with a lower concentration, and for the largest model, the new S-Se dimmers formed associated with the fourth Mo atom over the edge. This behavior is counterintuitive if compared with the traditional dichalcogenides, whose catalytic activity has been associated with the edges since the basal plane is inactive<sup>31</sup>. However, our results are consistent with the experimental observation of the Lou et al. group, where the Se face of the  $MoSSe$  structure surpasses the efficiency for the HER followed by the S face, the  $MoSe_2$ , and the  $MoS_2$ <sup>23</sup>.

These results are important to determine the preferential activity of the faces. However, a future study of the energetics of the reactions is necessary to determine the preferential reaction routes under energy restrictions. These results are beyond the

scope of this work and constitute a undergo project.

## Summary

We have used spin-polarized total energy calculations to study the atomic arrangement of MoSSe quantum dots with different edge terminations and exposure of the border atoms. Our findings show that structures C1, obtained from the Mo(10 $\bar{1}$ 0) termination with S/Se dimmers decorating each Mo from the edge and C2 from the S( $\bar{1}$ 010) termination with a zig-zag edge formed by protruding S-Se dimers bonded with two adjacent Mo atoms remain the most stable models; their slight difference in energy implies the coexistence of both structures. Both configurations tend to adopt a simple-concave morphology. However, C1 is curved to a lesser degree than C2. The geometrical distortion analysis reveals that the bond distribution in C1 is uniform as the S-Se dimmers of the edges tend to stabilize it; the opposite trend is observed in C2. The bond distributions showed that structural properties are modified as the size of the system is altered. This observation hints that the catalytic activity is conditioned on the edge termination and by the size.

TH-STM constant current images showed the absence of metallic states over the edge for both faces; in contrast, both configurations showed a greater contribution coming from a triangular section formed by S/Se atoms enclosed by the S-Se dimers over the edge. The constant height images also confirmed these contributions.

Finally, hypothetical reactive points were obtained by the EPI analysis. The results show that the S side poses a major electron density concentration than the Se side. Moreover, C1 displays an electronic distribution that points toward the preferential activity of the basal plane; the same trend emerges for C2, where the full-face displays a uniform distribution except for the S-Se dimers that emerge by size effects. These results are relevant to define the preferential activity of the faces. However, a future investigation to study energetics on model reactions is mandatory to define the preferential reaction routes.

## Methods

The stability of MoSSe quantum dots as a function of their size and termination has been analyzed by spin-polarized total-energy calculations through density functional theory as implemented in the Vienna ab initio simulation package<sup>32–36</sup>. Exchange-correlation energies were treated within the generalized gradient framework (GGA) with a Perdew-Burke-Ernzerhof (PBE) functional<sup>37</sup>. Valence states were represented by the frozen core approach by the projected augmented waves method<sup>38</sup>. The electronic states of the pseudo-wave function were modeled with an expansion of plane waves with an optimized cutoff energy of 500 eV. The energy corrections for the long-range interactions were taken into account by the Grimme-D3 method<sup>39</sup>. The supercell method was applied to isolate and impose periodic conditions between neighboring images of the MoSSe quantum dots with a separation distance of 13 Å. The force and energy criteria employed for the structural optimization were achieved when differences were lower than 0.01 eV/Å and  $1 \times 10^{-4}$  eV. The Brillouin zone was sampled with a gamma-centered k-point grid as implemented in the Monkhorst-Pack scheme<sup>40</sup>.

### 0.6 Formation energy formalism

To study the stability of different sizes and terminations of MoSSe quantum dots, we have employed the surface formation energy formalism (SFE). Our analysis takes as reference the  $MoS_2$  bulk to compare the stability of the layered structures  $1H - MoS_2$  against  $1H - MoSSe$  and different size MoSSe quantum dots. The SFE per atom considers the chemical potentials of each atomic species with the general formula  $Mo_xS_ySe_z$ .

$$SFE(\mu_{Mo}, \mu_{Se}, \mu_S) = \frac{E_{Mo_xS_ySe_z} - x\mu_{Mo} - y\mu_S - z\mu_{Se}}{x + y + z} \quad (1)$$

Where  $E_{Mo_xS_ySe_z}$  is the total energy of the quantum dot,  $\mu_X$  corresponds to the chemical potential of the X species, and x, y, and z are the number of Mo, S and Se atoms.

Thermal equilibrium between the bulk, vacuum, and molecular structure has been considered to establish the following correlation among chemical potentials.

$$\mu_{Mo}^{Bulk} + \mu_S^{Bulk} + \Delta H_f = \mu_{MoS_2} = \mu_{Mo} + 2\mu_S \quad (2)$$

Where  $\Delta H_f$  corresponds with the formation enthalpy of the reference -this is the  $MoS_2^{Bulk}$ - and the chemical potentials of the X species are inter-correlated with their corresponding bulk phases via:

$$\mu_X \leq \mu_X^{Bulk} \quad (3)$$

since

$$\mu_{\text{MoS}_2}^{\text{Bulk}} = \mu_{\text{Mo}} + 2\mu_{\text{S}} \quad (4)$$

The SFE can be rewritten considering equations 1 and 4 as follows.

$$SFE(\mu_{\text{Se}}, \mu_{\text{S}}) = \frac{E_{\text{Mo}_x\text{S}_y\text{Se}_z} - x\mu_{\text{MoS}_2}^{\text{Bulk}} - y\mu_{\text{S}}(2x - z) - z\mu_{\text{Se}}}{x + y + z} \quad (5)$$

## References

1. Tanwar, S., Arya, A., Gaur, A. & Sharma, A. L. Transition metal dichalcogenide (tmds) electrodes for supercapacitors: A comprehensive review. *J. Physics: Condens. Matter* (2021).
2. Nappini, S. *et al.* Transition-metal dichalcogenide nite2: An ambient-stable material for catalysis and nanoelectronics. *Adv. Funct. Mater.* **30**, 2000915, DOI: <https://doi.org/10.1002/adfm.202000915> (2020). <https://onlinelibrary.wiley.com/doi/pdf/10.1002/adfm.202000915>.
3. Yun, Q. *et al.* Layered transition metal dichalcogenide-based nanomaterials for electrochemical energy storage. *Adv. Mater.* **32**, 1903826, DOI: <https://doi.org/10.1002/adma.201903826> (2020). <https://onlinelibrary.wiley.com/doi/pdf/10.1002/adma.201903826>.
4. Ji, H. G., Solís-Fernández, P., Erki1iç, U. & Ago, H. Stacking orientation-dependent photoluminescence pathways in artificially stacked bilayer ws2 nanosheets grown by chemical vapor deposition: Implications for spintronics and valleytronics. *ACS Appl. Nano Mater.* **4**, 3717–3724, DOI: [10.1021/acsanm.1c00192](https://doi.org/10.1021/acsanm.1c00192) (2021).
5. Sanikop, R. & Sudakar, C. Tailoring magnetically active defect sites in mos2 nanosheets for spintronics applications. *ACS Appl. Nano Mater.* **3**, 576–587, DOI: [10.1021/acsanm.9b02121](https://doi.org/10.1021/acsanm.9b02121) (2020).
6. Noh, S. H. *et al.* Tuning the catalytic activity of heterogeneous two-dimensional transition metal dichalcogenides for hydrogen evolution. *J. Mater. Chem. A* **6**, 20005–20014, DOI: [10.1039/C8TA07141A](https://doi.org/10.1039/C8TA07141A) (2018).
7. Guo, Y. *et al.* Distinctive in-plane cleavage behaviors of two-dimensional layered materials. *ACS Nano* **10**, 8980–8988, DOI: [10.1021/acs.nano.6b05063](https://doi.org/10.1021/acs.nano.6b05063) (2016).
8. Ellis, J. K., Lucero, M. J. & Scuseria, G. E. The indirect to direct band gap transition in multilayered mos2 as predicted by screened hybrid density functional theory. *Appl. Phys. Lett.* **99**, 261908, DOI: [10.1063/1.3672219](https://doi.org/10.1063/1.3672219) (2011). <https://doi.org/10.1063/1.3672219>.
9. Ciccarino, C. J., Christensen, T., Sundararaman, R. & Narang, P. Dynamics and spin-valley locking effects in monolayer transition metal dichalcogenides. *Nano Lett.* **18**, 5709–5715, DOI: [10.1021/acs.nanolett.8b02300](https://doi.org/10.1021/acs.nanolett.8b02300) (2018).
10. Yin, W.-J. *et al.* The unique carrier mobility of monolayer janus mosse nanoribbons: a first-principles study. *Dalton Trans.* –, DOI: [10.1039/D1DT01121A](https://doi.org/10.1039/D1DT01121A) (2021).
11. Han, G. H., Duong, D. L., Keum, D. H., Yun, S. J. & Lee, Y. H. van der waals metallic transition metal dichalcogenides. *Chem. Rev.* **118**, 6297–6336, DOI: [10.1021/acs.chemrev.7b00618](https://doi.org/10.1021/acs.chemrev.7b00618) (2018).
12. Choi, W. *et al.* Recent development of two-dimensional transition metal dichalcogenides and their applications. *Mater. Today* **20**, 116–130, DOI: <https://doi.org/10.1016/j.mattod.2016.10.002> (2017).
13. Manzeli, S., Ovchinnikov, D., Pasquier, D., Yazyev, O. V. & Kis, A. 2d transition metal dichalcogenides. *Nat. Rev. Mater.* **2**, 17033 (2017).
14. Mitra, S. *et al.* Tailoring phonon modes of few-layered mos2 by in-plane electric field. *npj 2D Mater. Appl.* **4**, 6 (2020).
15. Chhowalla, M. *et al.* The chemistry of two-dimensional layered transition metal dichalcogenide nanosheets. *Nat. Chem.* **5**, 263–275, DOI: [10.1038/nchem.1589](https://doi.org/10.1038/nchem.1589) (2013).
16. Helveg, S. *et al.* Atomic-scale structure of single-layer mos2 nanoclusters. *Phys. Rev. Lett.* **84**, 951–954, DOI: [10.1103/PhysRevLett.84.951](https://doi.org/10.1103/PhysRevLett.84.951) (2000).
17. Yagmurcukardes, M. *et al.* Quantum properties and applications of 2d janus crystals and their superlattices. *Appl. Phys. Rev.* **7**, 011311, DOI: [10.1063/1.5135306](https://doi.org/10.1063/1.5135306) (2020). <https://doi.org/10.1063/1.5135306>.

18. Riis-Jensen, A. C., Deilmann, T., Olsen, T. & Thygesen, K. S. Classifying the electronic and optical properties of janus monolayers. *ACS Nano* **13**, 13354–13364, DOI: [10.1021/acsnano.9b06698](https://doi.org/10.1021/acsnano.9b06698) (2019).
19. Mikkelsen, A. E. G., Bølle, F. T., Thygesen, K. S., Vegge, T. & Castelli, I. E. Band structure of moste janus nanotubes. *Phys. Rev. Mater.* **5**, 014002, DOI: [10.1103/PhysRevMaterials.5.014002](https://doi.org/10.1103/PhysRevMaterials.5.014002) (2021).
20. Petrić, M. M. *et al.* Raman spectrum of janus transition metal dichalcogenide monolayers wsse and mosse. *Phys. Rev. B* **103**, 035414, DOI: [10.1103/PhysRevB.103.035414](https://doi.org/10.1103/PhysRevB.103.035414) (2021).
21. Jin, C. *et al.* A janus mosse monolayer: a superior and strain-sensitive gas sensing material. *J. Mater. Chem. A* **7**, 1099–1106, DOI: [10.1039/C8TA08407F](https://doi.org/10.1039/C8TA08407F) (2019).
22. Zhang, J. *et al.* Janus monolayer transition-metal dichalcogenides. *ACS Nano* **11**, 8192–8198, DOI: [10.1021/acsnano.7b03186](https://doi.org/10.1021/acsnano.7b03186) (2017). PMID: 28771310, <https://doi.org/10.1021/acsnano.7b03186>.
23. Lu, A.-Y. *et al.* Janus monolayers of transition metal dichalcogenides. *Nat. Nanotechnol.* **12**, 744–749, DOI: [10.1038/nnano.2017.100](https://doi.org/10.1038/nnano.2017.100) (2017).
24. Lauritsen, J. V. *et al.* Size-dependent structure of mos2 nanocrystals. *Nat. Nanotechnol.* **2**, 53–58, DOI: [10.1038/nnano.2006.171](https://doi.org/10.1038/nnano.2006.171) (2007).
25. Zhang, H., He, H., Jiang, X., Xia, Z. & Wei, W. Preparation and characterization of chiral transition-metal dichalcogenide quantum dots and their enantioselective catalysis. *ACS Appl. Mater. & Interfaces* **10**, 30680–30688, DOI: [10.1021/acsnano.7b03186](https://doi.org/10.1021/acsnano.7b03186) (2018).
26. Joo, P. H., Cheng, J. & Yang, K. Size effects and odd–even effects in mos2 nanosheets: first-principles studies. *Phys. Chem. Chem. Phys.* **19**, 29927–29933, DOI: [10.1039/C7CP05402E](https://doi.org/10.1039/C7CP05402E) (2017).
27. Shu, H. *et al.* The capacity fading mechanism and improvement of cycling stability in mos2-based anode materials for lithium-ion batteries. *Nanoscale* **8**, 2918–2926, DOI: [10.1039/C5NR07909H](https://doi.org/10.1039/C5NR07909H) (2016).
28. O’Hare, P., Lewis, B. M. & parkinson, B. Standard molar enthalpy of formation by fluorine-combustion calorimetry of tungsten diselenide (wse2). thermodynamics of the high-temperature vaporization of wse2. revised value of the standard molar enthalpy of formation of molybdenite (mos2). *The J. Chem. Thermodyn.* **20**, 681–691, DOI: [https://doi.org/10.1016/0021-9614\(88\)90019-5](https://doi.org/10.1016/0021-9614(88)90019-5) (1988).
29. Besenbacher, F. *et al.* Recent stm, dft and haadf-stem studies of sulfide-based hydrotreating catalysts: Insight into mechanistic, structural and particle size effects. *Catal. Today* **130**, 86–96, DOI: <https://doi.org/10.1016/j.cattod.2007.08.009> (2008). New developments in sulfide catalysis: Linking industrial needs to fundamental challenges.
30. Tersoff, J. & Hamann, D. R. Theory of the scanning tunneling microscope. *Phys. Rev. B* **31**, 805–813, DOI: [10.1103/PhysRevB.31.805](https://doi.org/10.1103/PhysRevB.31.805) (1985).
31. Wang, Z. *et al.* Controllable etching of mos2 basal planes for enhanced hydrogen evolution through the formation of active edge sites. *Nano Energy* **49**, 634–643, DOI: <https://doi.org/10.1016/j.nanoen.2018.04.067> (2018).
32. Hohenberg, P. & Kohn, W. Inhomogeneous electron gas. *Phys. Rev.* **136**, B864–B871, DOI: [10.1103/PhysRev.136.B864](https://doi.org/10.1103/PhysRev.136.B864) (1964).
33. Kohn, W. & Sham, L. J. Self-consistent equations including exchange and correlation effects. *Phys. Rev.* **140**, A1133–A1138, DOI: [10.1103/PhysRev.140.A1133](https://doi.org/10.1103/PhysRev.140.A1133) (1965).
34. Kresse, G. & Hafner, J. Ab initio molecular dynamics for liquid metals. *Phys. Rev. B* **47**, 558–561, DOI: [10.1103/PhysRevB.47.558](https://doi.org/10.1103/PhysRevB.47.558) (1993).
35. Kresse, G. & Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **54**, 11169–11186, DOI: [10.1103/PhysRevB.54.11169](https://doi.org/10.1103/PhysRevB.54.11169) (1996).
36. Kresse, G. & Furthmüller, J. Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Comput. Mater. Sci.* **6**, 15 – 50, DOI: [https://doi.org/10.1016/0927-0256\(96\)00008-0](https://doi.org/10.1016/0927-0256(96)00008-0) (1996).
37. Perdew, J. P., Burke, K. & Ernzerhof, M. Generalized gradient approximation made simple. *Phys. Rev. Lett.* **77**, 3865–3868, DOI: [10.1103/PhysRevLett.77.3865](https://doi.org/10.1103/PhysRevLett.77.3865) (1996).
38. Kresse, G. & Joubert, D. From ultrasoft pseudopotentials to the projector augmented-wave method. *Phys. Rev. B* **59**, 1758–1775, DOI: [10.1103/PhysRevB.59.1758](https://doi.org/10.1103/PhysRevB.59.1758) (1999).
39. Grimme, S., Antony, J., Ehrlich, S. & Krieg, H. A consistent and accurate ab initio parametrization of density functional dispersion correction (dft-d) for the 94 elements h-pu. *The J. Chem. Phys.* **132**, 154104, DOI: [10.1063/1.3382344](https://doi.org/10.1063/1.3382344) (2010). <https://doi.org/10.1063/1.3382344>.

40. Monkhorst, H. J. & Pack, J. D. Special points for brillouin-zone integrations. *Phys. Rev. B* **13**, 5188–5192, DOI: [10.1103/PhysRevB.13.5188](https://doi.org/10.1103/PhysRevB.13.5188) (1976).

## **Acknowledgements**

We thank Conacyt grant A1-S-33492 of the Call of Proposals for Basic Scientific Research, DGAPA-UNAM projects IA100920, IN110820, and IG200320 for partial financial support. Calculations were performed in the DGCTIC-UNAM Supercomputing Center, projects LANCAD-UNAM-DGTIC-368 and LANCADUNAM- DGTIC-150. We thank Aldo Rodriguez-Guerrero for technical support. R.P.-P. and H.N.F.E. acknowledge DGAPAUNAM for the postdoctoral position.

## **Author contributions statement**

J.I.P. writing and performing the calculations, R.P.P. conceptualization and supporting algorithms, H.N.F. writing and data software development, D.M.H. validation, E.A.M. data presentation, M.G.M. resources and supervision ,D.H.G. supervision and formal analysis, and J.G.S. conceived and conducted the investigation. All authors have reviewed the manuscript.

## **Additional information**

### **Competing interests**

The authors declare that there are no competing interest to declare.